

The Influence of the Relative Sliding on the Surface Quality

This paper presents a study on the surface quality pointing out the influence of relative sliding on the topography parameters. Traditional roughness parameters as R_a and R_q , deal only with relative high of the asperities to the mean line and they give no information on shape, slope and asperities magnitude, on their appearance frequency on the profile length. The authors analysed a set of 3D parameters including the amplitude ones (S_a , S_{ku} , S_{sk} and S_t) and functional parameters as S_{vk} , S_k and S_{pk} as calculated with a dedicated soft from the bearing area. Tests were done on roller-roller tribotester lubricated with the grease grade UM185Li2EP (general purpose grease for rolling bearings), the temperature of the environment being kept at 80°C. There was studied the influence of relative sliding speed on the skewness and the kurtosis of the surface topography, but also on common parameters as S_a and S_t . Such a study may be used for selecting a suitable surface quality and to evaluate the surface topography degradation in time, after tests under severe conditions, very close to the actual ones.

Keywords: roller-roller tribotester, relative sliding, profilometry, functional 3D parameters.

1. INTRODUCTION

Traditional roughness parameters as R_a and R_q , deal only with relative high of asperities to the mean line and they give no information on shape, slope and asperities magnitude, on their appearance frequency on the profile length.

3D profilometry offers the opportunity for a deeper and more accurate analysis of the surface quality [3-5].

Multiple measurements in different areas on the sample can produce results within a large range, due to variations of the surface texture across the sample surface. Consequently, the results of any single measurement may not be representative of the overall surface quality [3, 4] and specialists recommend methods to be applied for a more accurate characterisation of the surface, more often for manufactured parts, and rarely for evaluating how the surface quality evolved in actual exploitation.

The parameters involved in this study are briefly described below. The analysed amplitude parameters are: the roughness average, S_a [μm], the root mean square S_q [μm], the surface skewness, S_{sk} [-], the surface kurtosis, S_{ku} [-], the peak-peak height, S_t [μm].

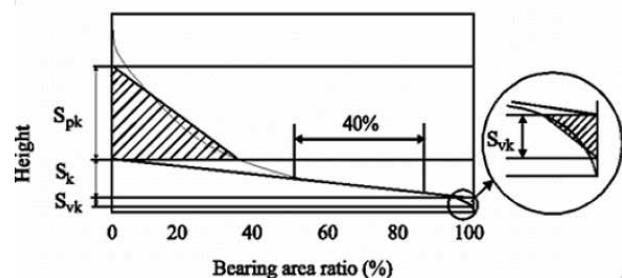


Figure 1. Bearing curve illustrating the calculation of S_{pk} , S_k and S_{vk} [6]

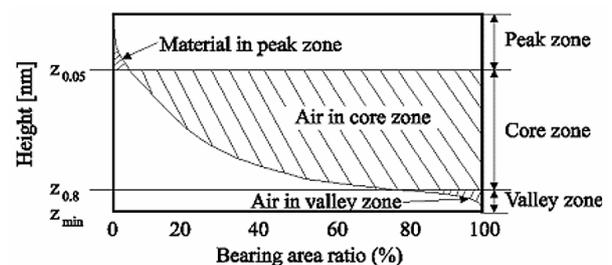


Figure 2. Bearing curve illustrating the calculation of S_{bi} , S_{ci} and S_{vi} [6]

Nicolae Diaconu, Lorena Deleanu, Florentina Potecaşu, Sorin Ciortan
Dunarea de Jos” University, Romania,
E-mail: nicolae.diaconu@ugal.ro

The functional parameters are described graphically in Figures 1 and 2.

The surface bearing index, Sbi [μm], is defined as:

$$Sbi = \frac{Sq}{Z_{0.05}} \quad (1)$$

where $Z_{0.05}$ is the distance from the top of the surface to the height at 5% bearing area.

The core fluid retention index, Sci [μm], is defined as:

$$Sci = \frac{V_v(h_{0.05}) - V_v(h_{0.080})}{(M-1)(N-1)\delta x \cdot \delta y} Sq \quad (2)$$

where $V_v(Z_x)$, is the void area over the bearing area ratio curve and under the horizontal line Z_x .

The valley fluid retention index, Svi [μm], is defined as:

$$Svi = \frac{V_v(h_{0.80})}{(M-1)(N-1)\delta x \cdot \delta y} \quad (3)$$

For relations (1)...(3), M is the number of lines of the investigated area and N are the number of points on each line.

The reduced summit height, Spk , is the height of the upper left triangle [6]. The core roughness depth, Sk , is the height difference between the intersection points of the found least mean square line. The reduced valley depth, Svk , is the height of the triangle drawn at 100% (Figure 1).

2. TESTING METHODOLOGY

Tests were done on a roller-roller tribotester (Fig. 1) [2]. The test conditions were: normal load $Q=1.0$ kN, enclosure temperature $\theta=80^\circ\text{C}$, rolling speed (for $\xi=0\%$) $v=1.09$ m/s, testing period $t=240$ minutes, lubricant: grease grade UM185Li2EP (general purpose grease for rolling bearings), diameter of rollers for pure rolling $D=42.0$ mm, contact width $B=10$ mm ($B_{\text{roller1}}=10$ mm, $B_{\text{roller2}}=12$ mm)

The relative sliding between rollers was pointed out by the sliding coefficient, calculated as:

$$\xi = \frac{2(v_1 - v_2)}{v_1 + v_2} \cdot 100 [\%] \quad (4)$$

v_1 and v_2 being the peripheral speeds for the roller 1 and 2, respectively. $\xi=0$ is for pure rolling.

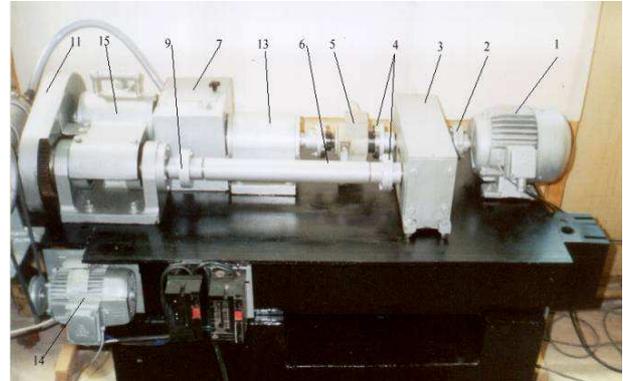


Figure 3. The testing machine 1– driving electric engine; 2, 4, 9– rigid coupling; 3– gear transmission; 5– torque transducer; 6– intermediate shaft; 7– thermoisolant box; 8 – tested rollers (in box 7); 10– force transducer; 11– reducing gear box.

The roller geometry allows running the test with three values for the relative sliding: $\xi=0\%$ (pure rolling), $\xi=16.3\%$ and $\xi=33.5\%$.

Rollers were made of heat-treated high-quality carbon steel. All rollers were grinded and the topography parameters are given in all figures as for unworn surfaces. The rollers 3A, 5C, 1E and 4A are made of steel grade OLC25 (0.25% C) and the rollers 3B, 5D, 1F are made of steel grade OLC45 (0.45% C). The investigated pairs of rollers are: 3A-3B, 5C-5D, 1E-1F and 4A-4B.

There were investigated square areas of $500\mu\text{m} \times 500\mu\text{m}$, in the central zone of the wear track with the help of a CETR contact profilometer. The vertical range was set up to $500 \mu\text{m}$ as wear tracks had visible traces in the sliding direction and the scan speed was set at $35 \mu\text{m/s}$. This research was done for 200 points per line and the step between lines was selected at $5 \mu\text{m}$. All parameters are calculated from the raw profiles that “rebuild” the actual surface [6]. The stylus equivalent loading force was set at 28 mg for all measurements.

A single 3D measurement is usually insufficient for the grading of a surface, if a specific parameter value is desired. It is

recommended a standard number of five sampling length for 2D parameters [7, 8] and the number of line samples are 100 for all three measurements on each wear track, but someone could say these are too “concentrated” in a small area of the surface of interest. It was

found that it is often necessary to perform at least 5 measurements to obtain a stable mean value for many roughness parameters while others need a larger number as there is often one or few measurements diverging from the expected normally distributed result [1, 4, 8].

Table 1. Example of data for the roller 5C.

3D parameter	Sample 5C_1	Sample 5C_2	Sample 5C_3	Average	MAX	MIN	As	Ai	As (%)	Ai (%)
Sa	0.371	0.376	0.373	0.373	0.376	0.371	0.003	-0.002	0.68	-0.59
Sq	0.489	0.601	0.537	0.542	0.601	0.489	0.058	-0.053	10.787	-9.74
Ssk	-0.676	1.770	-2.939	-0.615	1.770	-2.939	2.385	-2.324	-387.84	377.92
Sku	7.188	39.160	21.375	22.574	39.160	7.188	16.586	-15.386	73.47	-68.15
St	6.268	13.290	7.030	8.863	13.290	6.268	4.428	-2.595	49.95	-29.27
Spk	0.634	4.367	0.135	1.712	4.367	0.135	2.655	-1.577	155.09	-92.10
Sk	1.099	0.829	0.804	0.910	1.099	0.804	0.189	-0.107	20.72	-11.74
Svk	0.618	0.685	0.919	0.741	0.919	0.618	0.178	-0.123	24.08	-16.59

Table 1. contains the results with 3 digits after point for easy reading, all operations being done with 5 digits after point.

For worn surfaces the number of measurements will be established depending on surfaces to be investigated. Here the authors did 3 measurements for each roller and there were calculated the average values of the 3D amplitude parameters and several functional parameters as obtained from raw (non-filtered) (examples are given in table 1 and Figure 9). $As\%(S_x)$ is the percentage of up-deviation from the calculated average value:

$$\begin{aligned}
 As\%(S_x) &= \frac{Max(S_x) - Average(S_x)}{Average(S_x)} 100 = \\
 &= \frac{As(S_x)}{Average(S_x)} [\%] \quad (4)
 \end{aligned}$$

$Ai\%(S_x)$ is the percentage of the inferior deviation from the calculated average value:

$$\begin{aligned}
 Ai(S_x) &= \frac{Min(S_x) - Average(S_x)}{Average(S_x)} 100 = \\
 &= \frac{Ai}{Average(S_x)} [\%] \quad (5)
 \end{aligned}$$

In relationships (4) and (5), S_x is one of the parameters $Sa, Sq, St, Sku, Ssk, Sbi, Sci, Svi, Sk, Spk, Svk$. $Max(S_x)$ is the maximum value of all measurements for parameter S_x , $Min(S_x)$ is the minimum value of all measurements for parameter S_x and $Average(S_x)$ is the average value of all measurements for parameter the same S_x .


Filtered profiles could disturb the values [3, 4], especially for high peaks and deep valleys that are important to be pointed out on worn surfaces.

3. CONCLUSION

Figure 4. presents the amplitude parameters Sa, Sq and St . As mentioned in [1, 3, 4] Sa is not a reliable parameter for assessing the surface quality, especially for worn surfaces. For all investigated surfaces Sa is lower than the value obtained for grinded (unworn) surfaces and even Sq seems to have the same tendency and both ones could be considered less sensitive to relative sliding. St has a clear trend to be reduced for both rollers under pure rolling, but at $\xi=16.3\%$, there were recorded the highest values meaning that this value could generate the highest peaks. These are dangerous especially for lubricated contacts because they incapacitate for generating a continuous film of lubricant and increase the probability of direct contacts among asperities.

Sku increases for all tested surfaces, but especially for rollers with relative sliding, meaning that the relative sliding could generate a distribution with rare but narrow peaks. The values are much lower for the steel grade OLC45 and for this steel grade the influence of relative sliding seems to be almost linear under the test conditions. For the steel grade OLC 25 both values of relative sliding have generated close values for this parameter. Sku has the largest spread range,

about 8...9 times greater than the initial value. Figure 8 presents images of the worn surfaces as being rebuilt based on the measured coordinates and these images reveal isolated deep valleys.

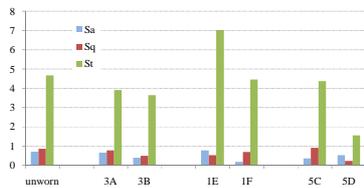


$\xi=0\%$ $\xi=16.3\%$ $\xi=33.6\%$

Figure 4. Amplitude parameters Sa , Sq and St for the tested rollers

The negative values for Ssk point out there are holes in the surface topography, deeper for $\xi=16.3\%$ and for this test, for the roller made of steel grade OLC25.

Ssk has a similar trend for the highest relative slide ($\xi=33.5\%$). Due to this value the asperities are “micro-grinded” and Ssk is similar to the initial ones. High relative changes of these two parameters (Ssk and Sku) for the worn surfaces are also reported by Krzyzak in [5].

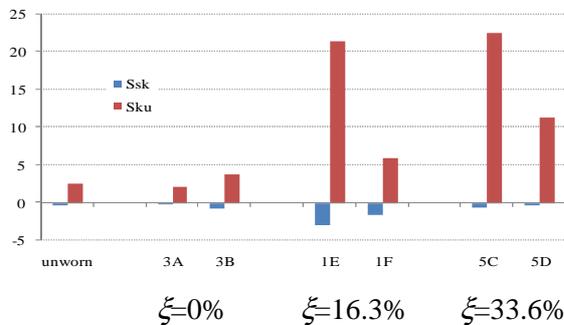


$\xi=0\%$ $\xi=16.3\%$ $\xi=33.6\%$

Figure 5. Amplitude parameters Ssk and Sku for the tested rollers

If one analyses only the average parameter Sa , he will notice that it remains close to the initial value, or even lower, but the conclusion that surface become smother is a “false friend” and additional information is necessary for describing it. For instance, St – the maximum peak-to-valley value on the investigated areas, increases for roller tested under relative sliding, but for the rollers under pure rolling, the parameters like Sa , Sk and St are smaller with 20...25%. Even Sa for all tested rollers remains in a range considered good for further exploitation, the higher values for St

offers the motivation of harder damages on rollers 5C-5D and 1E-1F.

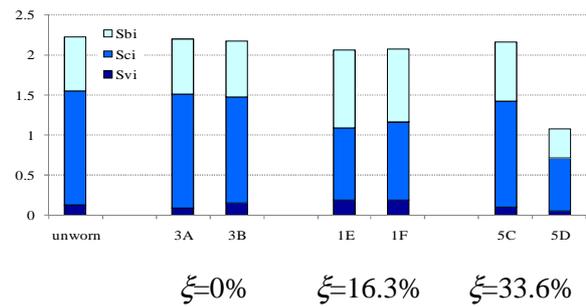

$\xi=0\%$ $\xi=16.3\%$ $\xi=33.6\%$

Figure 6. Functional parameters Sbi , Sci and Svi for the tested rollers


For $\xi=0\%$ and $\xi=33.6\%$ the functional parameters Svk , Sk and Spk are reduced as compared to the initial surface, but for $\xi=16.3\%$ the sum of these parameters is higher, Svk and Sk being much higher as compared to the unworn surface (Figure 7).

A comparative study of the surface topography, obtained by changing a single parameter during the tests, may reveal at least a qualitative influence of this parameter that could be useful for practitioners.

There could be noticed two groups of parameters:

- parameters less influenced by the relative sliding, including Sa , Sq ,
- parameters bearing a greater influence, these being Ssk and Sku and the functional parameters.

Taking into account the ranging of the calculated parameters, one may notice that Sa , Sq , Svk and Sk have a narrow spreading range, a second group may include parameters with a range similar to the parameter value (50...100%), e.g. St and Sku . A special attention has to be paid to Ssk that could have the spreading range much greater as compared to the average value.

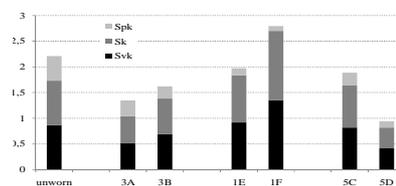

$\xi=0\%$ $\xi=16.3\%$ $\xi=33.6\%$

Figure 7. Functional parameters Spk , Sk and Svk for the tested rollers

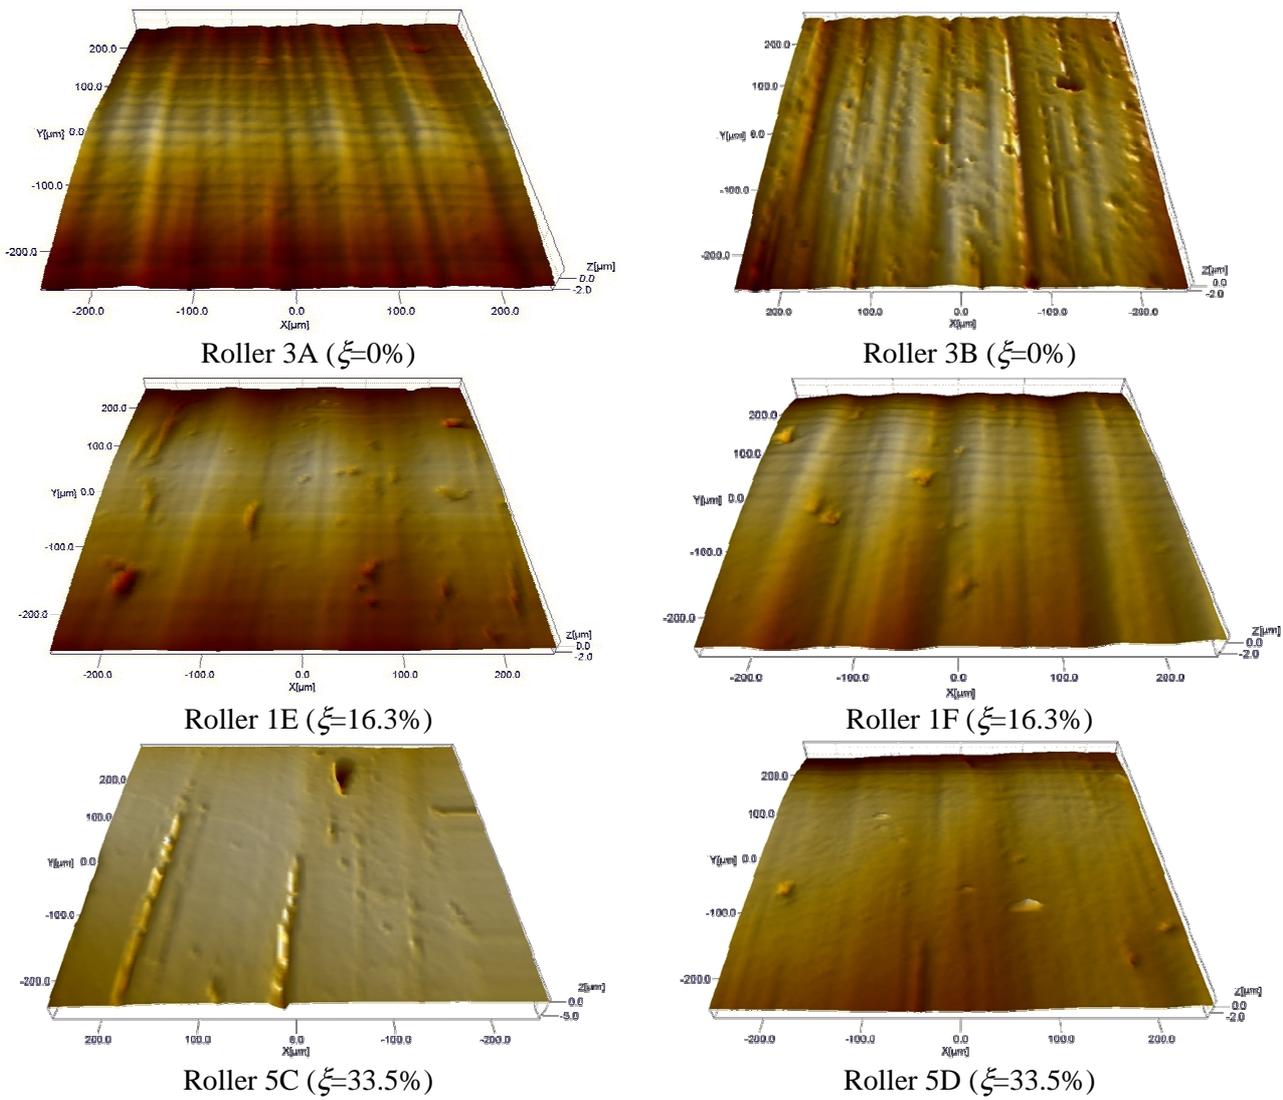


Figure 8. Virtual images of the investigated surfaces

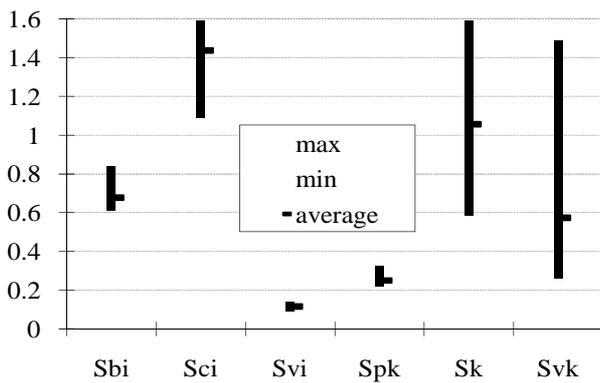


Figure 9. The spread range for functional parameters for roller 5C (three measurements on 500 x 500 μm each)

For pure rolling an increase of the normal load from 0.7 kN to 1.0 kN modifies the functional parameters as given in Figures 11-13, reducing the sum of these parameters as compared to the value obtained on unworn surface and that of tested at $Q=0.7$ kN.

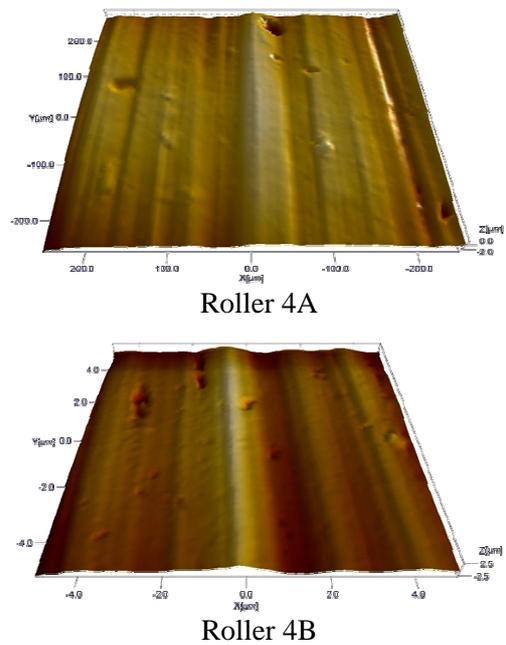


Figure 10. Virtual rebuilding of the tested surfaces for $Q=0.7$ kN, pure rolling

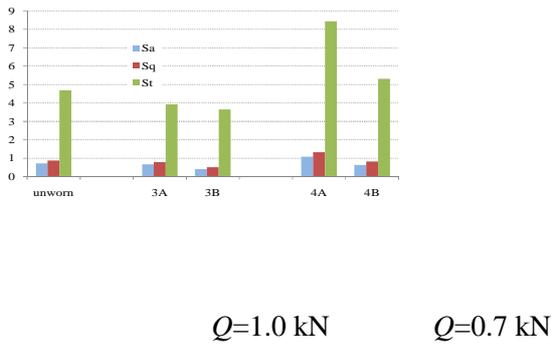


Figure 11. Amplitude parameters S_a , S_q and S_t for the roller surfaces under pure rolling

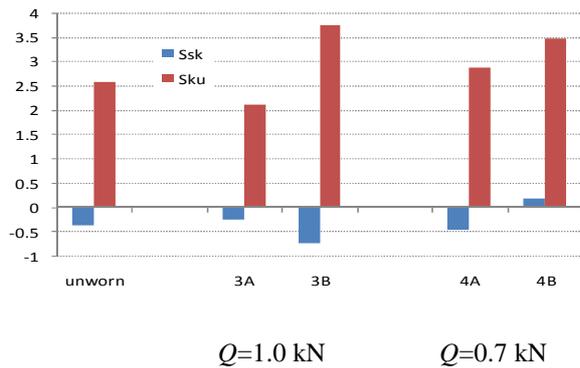


Figure 12. Amplitude parameters S_{sk} and S_{ku} for the roller surfaces under pure rolling

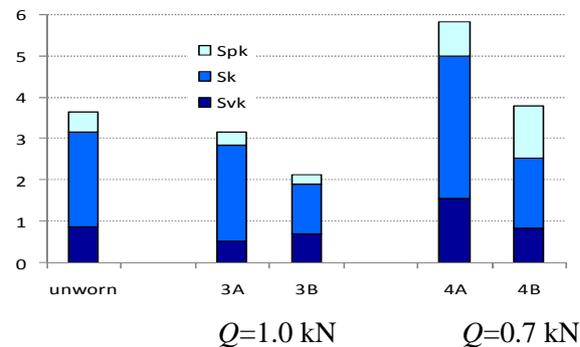


Figure 13. Functional parameters S_k , S_{pk} and S_{vk} for roller surfaces under pure rolling

Comparing images from Figure 8 (rollers 3A and 3B) and Figure 10 (rollers 4A and 4B), one may notice that the damaging processes of the surface are similar, but more intense for the rollers bearing $Q=1.0$ kN. The higher load reduced the amplitude parameters like S_a , S_k and S_t (Figure 11). S_{sk} remains in the negative range for $Q=1.0$ kN, but for $Q=0.7$ kN there were recorded values giving a positive average (Figure 12). Under this load and pure rolling, the higher isolated peaks may be less damaged as compared to those under a rolling-sliding motion. It could also be the consequence of adhesive wear (isolated high peaks above the surface could be seen in Figure 10, suggesting wear debris adhered on the roller surface).

Taking into account the surface quality, steel grade OLC45 is more appropriate for application with similar conditions as those involved in these tests as compared to the steel grade OLC 25, because many of the surface parameters have only a small increase, meaning the surfaces could continue to work under those conditions. A similar qualitative evaluation was obtained by analysing the virtual images of the tested surfaces as given by a dedicated soft of the 3D profilometer.

REFERENCES

- [1] N. Diaconu, *Influence of the testing parameters on the surface quality of steel roller-roller system under grease lubrication, paper 25347*, Proceedings of the 10th Biennial Conference on Engineering Systems Design and Analysis, ESDA10, July 12-14, Istanbul, Turkey, 2010
- [2] N. Diaconu, *Study on the Influence of the Working Environment on the Behaviour of Several Greases Used in Rolling and Rolling-Sliding Tribosystems* (in Romanian), PhD thesis, "Dunarea de Jos" University of Galati, 2001
- [3] L. Blunt, X. Jiang, *Advanced techniques for assessment surface topography development of a basis for 3D surface texture standards "surfstand"*, London; Sterling, VA, Kogan Page Science, Elsevier, 2003.
- [4] Whitehouse D.J., *Handbook of Surface and Nanometrology*, University of Warwick, Institute of Physics Publishing, Bristol and Philadelphia, 2003
- [5] Z. Krzyzak, P. Pawlus, *'Zero-wear' of piston skirt surface topography*, Wear 260, pp. 554–561, 2006.
- [6] The Scanning Probe Image Processor SPIPTM, Version 4.7 (2008).
- [7] SR EN ISO 12085:1999 Geometrical Product Specifications (GPS). Surface texture: Profile method. Motif parameters and SR EN ISO 12085:1999/AC:2009 Geometrical product specifications (GPS). Surface texture: Profile method. Motif parameters
- [8] SR EN ISO 13565-2:1999 Geometrical Product Specifications (GPS). Surface texture: Profile method; Surfaces having stratified functional properties. Part 2: Height characterization using the linear material ratio curve