

Enhancing the Tribo-Mechanical Properties of AISI 304 Steel Using Cladding Techniques: A Review

Rajeev Ranjan^{a,*} , Anil Kumar Das^a 

^aDepartment of Mechanical Engineering, National Institute of Technology Patna, Patna, Bihar, 800005, India.

Keywords:

Cladding
AISI 304 steel
Micro-hardness
Wear resistance
Microstructure

* Corresponding author:

Rajeev Ranjan
E-mail: rajeevranjan.br@gmail.com

Received: 5 September 2025
Revised: 18 October 2025
Accepted: 4 November 2025



A B S T R A C T

AISI 304 steel has limited use in several applications because of its high friction coefficient, insufficient hardness, and inadequate resistance to wear. Enhancing the tribological and mechanical characteristics of the material can be enhanced by applying a coating to its surface. Cladding, a surface modification method, is employed to form layers on the substrate with improved biocompatibility, durability, resistance to high-temperature oxidation, and mechanical strength. Proper material selection, along with appropriate cladding techniques and process parameters, is crucial for achieving these enhanced properties. Hard transition metals, metal matrix composites, alloys, ceramics, high-entropy alloys, nano-composites, rare earth oxides, and solid lubricants are frequently used to coat AISI 304 steel. The application of these coatings is to boost the hardness, wear resistance, corrosion-resistance, and extend the lifespan of steel. This study reviews the results of widely-used wear-resistant cladding methods applied to AISI 304 steel surfaces, while examining key functional claddings in detail. Contemporary problems and future perspectives are also reviewed, with a particular emphasis on identifying facts and technological gaps and proposing future research possibilities. It is recommended that future advancements in wear-resistant cladding should emphasize smart manufacturing techniques, optimize microstructural configurations, and develop numerical simulations for cladding processes to enhance toughness and hardness.

© 2026 Published by Faculty of Engineering

1. INTRODUCTION

Cladding is an efficient method for enhancing the surface properties of metallic and non-metallic parts by forming a high-quality coating of materials [1–3]. Heat sources with high energy, such as lasers, electron beams, and electric-arc welding techniques, have been successfully used

to achieve strong metallurgical bonds between the cladding and substrate materials [4–5]. Common cladding techniques such as laser cladding (LC), tungsten inert gas (TIG) cladding, plasma transferred arc (PTA) cladding, and high-velocity oxygen-fuel (HVOF) cladding, are widely applied in industry to coat surfaces with metals, ceramics, or a combination of both [6–9].

Stainless steel AISI 304 is frequently selected for producing machine parts, utensils, and structural elements due to its durability and excellent resistance to corrosion [10]. Its mechanical properties and durability in harsh environments make it suitable for use in variety of industries, such as nuclear and chemical industries, food processing equipment, petrochemical industries, condenser tubing, vapor lines, and heat exchangers [11-13]. However, the use of austenitic steel like AISI 304 is limited in applications where components face adhesive and abrasive wear, such as in agricultural and mining equipment, rock excavation tools, and dies used in manufacturing. Carbon may be added to stainless steels to boost their hardness, but doing so often decreases their ductility and degrades their overall performance [14]. Heat treatment also proves ineffective in hardening austenitic steel, as the process leads to the formation of chromium carbide (Cr_{23}C_6) along grain boundaries, depleting the steel of chromium and reducing its corrosion resistance [15]. Hard ceramic granules such as tungsten carbide (WC), titanium carbide (TiC), and silicon

carbide (SiC) can be added to the surface of austenitic steel to improve wear resistance by forming a composite clad layer that increases hardness. Various coating techniques have been explored to apply hard, wear-resistant coatings to steel substrates [16-18].

Various surface modification techniques have been employed for producing claddings on AISI 304 steel surfaces, as illustrated in Fig. 1. These techniques include metal inert gas (MIG) cladding, tungsten inert gas (TIG) cladding, laser cladding, and plasma arc cladding. The entire cladding process is presented in a flow chart format, with Fig. 2 providing a step-by-step breakdown of how the cladding layer is created on the substrate [18]. Initially, the surfaces were ground using sandpaper, and any organic residues were cleaned off with alcohol. Following that, a paste made of cladding powders and polyvinyl alcohol was applied onto the substrate with appropriate thickness to generate a green coating layer. Heat is then applied using different ways (as indicated in Fig. 1) to melt the powder; produce cladding with improved tribo-mechanical properties.

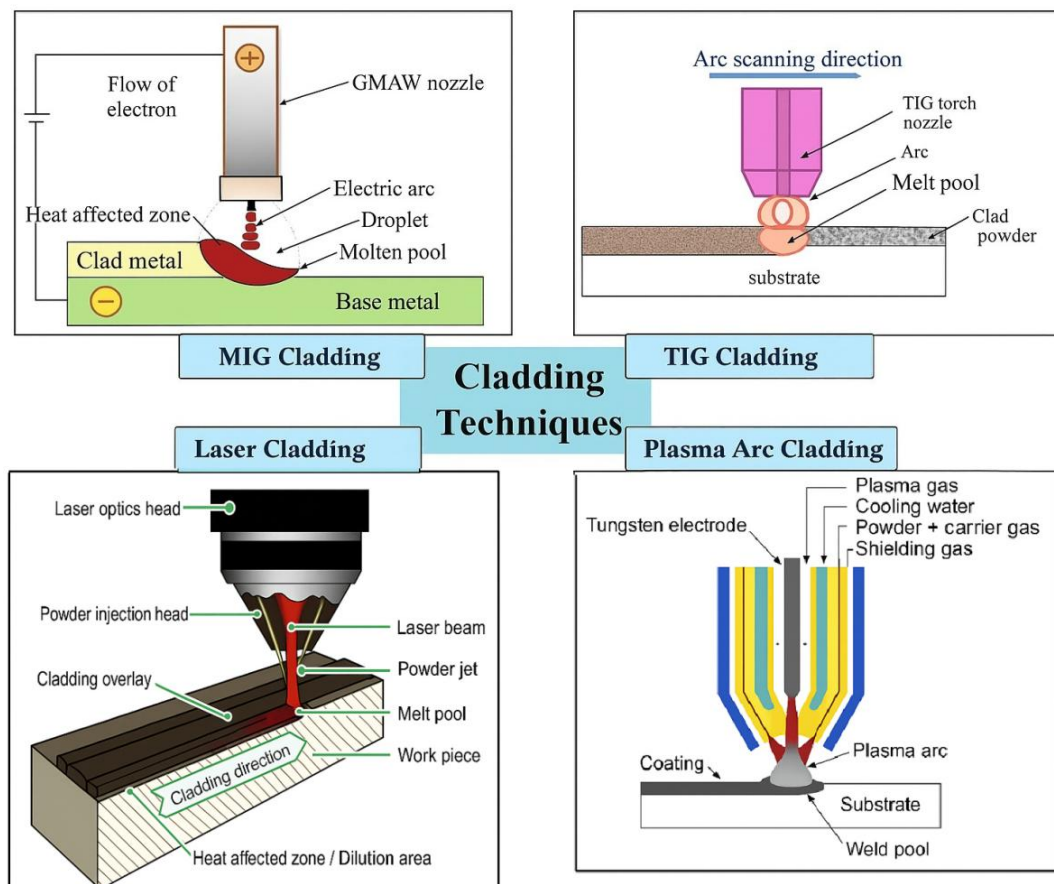


Fig. 1. Cladding techniques for AISI 304 steel substrate.

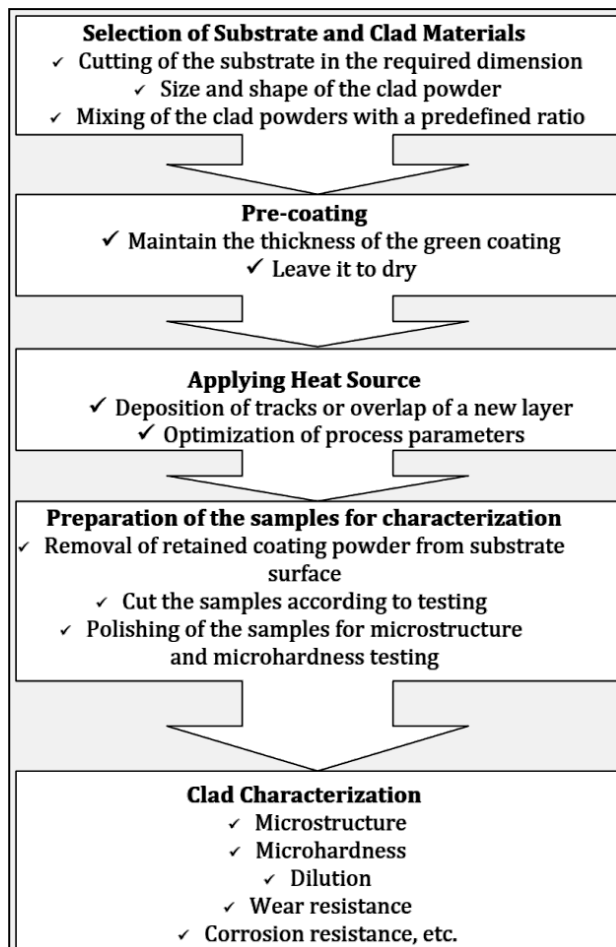


Fig. 2. Flow diagram illustrates the techniques used to create the cladding layer on a substrate.

Table 1 presents the various cladding techniques for AISI 304 steel investigated by earlier researchers. It also lists their

corresponding coating methods, key outcomes and research limitations of the studies. Among these, laser cladding has been identified as particularly advantageous for creating dense microstructures and strong metallurgical bonds with substrates. Researchers have extensively investigated the effects of laser cladding on AISI 304 steel to enhance its resistance to wear, high-temperature oxidation resistance, and biocompatibility. Recent progress in this field has focused on optimizing process parameters, refining cladding materials, and achieving specific material properties. However, challenges remain in the cladding of AISI 304 steel.

This article presents a comprehensive overview of surface modification techniques for AISI 304 steel using cladding techniques. It focuses on the benefits and uses of various cladding methods, as well as how different process parameters affect the microstructure and surface properties of the final clad layer. Additionally, the study discusses how optimizing process variables can improve the overall quality of cladding. This review serves as a useful resource for researchers in choosing appropriate coating powders and process parameters for thick cladding applications, and it also outlines potential future trends in this field of study.

Table 1. An overview of the cladding techniques used on AISI 304 steel.

Cladding Method	Coating/ Clad materials	Findings/ Results	Limitations	Authors (Ref.)
Laser Cladding	Titanium boride	Significantly enhancing wear resistance. Hardness improved up to 900HV (≈ 4.5 times increased)	Corrosion performance not analyzed	Majumdar et al. [11]
Plasma Arc Cladding	Ni–Cr–Si–B	Significantly enhancing micro-hardness (≈ 3.5 times increased)	Wear and corrosion performance not analyzed	Sudha et al. [19]
Laser Cladding	TiB ₂ –TiC–Al ₂ O ₃	Wear-rate reduced by 60% with respect to the substrate	Oxidation resistance not explored	Masanta et al. [16]
Laser Cladding	WC + Ni + NiCr	Produced fine-grained stainless steel with significantly enhancing micro-hardness (≈ 6 times increased)	Wear and corrosion behavior not studied	Anandan et al. [20]
Plasma sprayed	WC–Co	Wear-resistance improved nearly five times with respect to the substrate	Corrosion behavior unaddressed	Balamurugan et al. [21]
Plasma Arc Cladding	Ti–N–O	Hardness improved up to 1600HV (≈ 8 times increased)	Wear behavior unaddressed	Hsu et al. [22]

Thermal Spray	Ni-Base	Corrosion rate decreased by 50% in HCl solution	Wear behavior unaddressed	Sharma et al. [23]
Plasma sprayed	Hydroxyapatite-silicon oxide	Corrosion rate decreased by 60%	Mechanical strength and bonding strength unaddressed	Singh et al. [24]
Plasma Arc Cladding	TiAlN	Erosion rate reduced by 40% compared to the substrate	Wear behavior unaddressed	Grewal et al. [25]
Laser Cladding	Al ₂ O ₃	Hardness increased to 600HV (≈ 3 times over the substrate)	Effect of coating thickness on adhesion not examined	Xu 2014 [26]
Laser Cladding	TiC	Micro-hardness increased from 210HV to 1100HV	Did not explore resistance to wear	Sahoo et al. [27]
Laser Cladding	TiC	Hardness improved by 10 times as compared to the substrate	wear resistance not analyzed	Ushashri et al. [14]
Electrical discharge coating	TiC-Fe cermets	Hardness improved by 10 times as compared to the substrate	Tribological performance not investigated	Algoi et al. [28]
TIG cladding	TiC-Ni	Wear rate decreased by 70 times and hardness improved by 4.5 times	Oxidation and corrosion resistance not investigated	Sahoo et al. [29]
TIG cladding	TiC-Inconel825	Wear rate decreased by seven times and hardness improved by 5.5 times	Oxidation and corrosion resistance not investigated	Saroj et al. [30]
Thermal Spray	WC-CrC	Wear rate decreased by 65% compared to the substrate	Corrosion resistance not studied	Hajare et al. [31]
Laser Cladding	Tribaloy 400	Significantly enhancing wear resistance. Hardness improved up to 850HV (≈ 4 times increased)	Corrosion resistance not studied	Lin et al. [32]
Plasma Arc Cladding	TiC/CaF ₂ /γ-Ni	Hardness improved by 5.5 times and friction coefficient reduced by 40%	Corrosion resistance not studied	Liu et al. [33]
Plasma Arc Cladding	Al ₂ O ₃	The findings indicated that the porous coating increased and hence damping capacity improved by 35% over the substrate	Corelation of damping with coating thickness or porosity not investigated	Sachidananda et al. [34]
TIG cladding	Ni-201	Hardness improved by 1.5 times and corrosion rate decreased by 50%	Tribological performance not investigated	Shi et al. [35]
Magnetron sputtering	TiN	Hardness improved by 8 times and friction coefficient reduced to 0.35	Corrosion resistance not studied	Xi et al. [36]
Laser Cladding	AISI316	Dilution ratio reduced to 10%	Mechanical and corrosion performance not quantitatively analyzed	Apolinario et al. [37]
Laser Cladding	Ti and W	Resistance to wear of the coating was enhanced and hardness improved from 230HV to 900HV	The effect of multi-layer deposition not discussed	Dong et al. [38]
Sandblasting	Ni	Corrosion rate decreased by 45% in hydrochloric acid	Mechanical performance not quantitatively analyzed	Li et al. [39]
Laser Cladding	AlCrFeNi ₂ W _{0.2} Nbx	The microhardness improved by 4.5 times and wear rate reduced by 70%	Tribological behavior at elevated temperatures not studied	Liang et al. [40]
HVOF Spraying	NiCrSiB and Al ₂ O ₃	Wear resistance improved by 1.6 times and erosion rate reduced by 25%	Adhesion and fatigue properties not investigated	Praveen et al. [41]
Laser Cladding	NiCrBSi	Microhardness of coating 780HV (≈ 4 times improvement)	Corrosion aspects not investigated	zhang et al. [42]

Thermal Spray	Ti/TiN/TiSiN	Coefficiat of Friction reduced by 80% and wear resistance by 18.7 times	Long-term oxidation and fatigue behavior not studied	Alanagh et al. [43]
TIG cladding	Ni-Cr-B-Si	The microhardness improved by 4.5 times with dilution less than 8%	Tribological behavior not studied	Balaguru et al. [44]
HVOF-sprayed	Ni-20Cr2O3	Wear loss decreased by 55%	Oxidation and corrosion resistance not analyzed	Bansal et al. [45]
Laser Cladding	Stellite 12 and Ti/B4C	Microhardness increased upto 650HV and wear rate decreased by 50%	Oxidation and corrosion resistance not analyzed	Cheng et al. [46]
Plasma Arc Cladding	NiAl-Al2O3 + TiB2	Microstructure analysis revealed strong bonding between coating and the substrate, achieving hardness four times greater than the substrate	No corrosion or thermal cycling studies reported.	Imak et al. [47]
Laser Cladding	Ni60-TiC-WS2	Hardness increased to 302HV and COF reduced by 30%	Oxidation and corrosion resistance not analyzed	OuYang et al. [48]
Laser Cladding	Hastelloy C276TM alloy	Hardness increased to 850HV and wear loss reduced by 40%	Oxidation and corrosion resistance not analyzed	Rivero et al. [49]
TIG cladding	TiC-Ni	Hardness increased to 950HV and wear rate 70 times lower than the substrate	Corrosion and fatigue studies were not included.	sahu et al. [50]
TIG cladding	Inconel 825	Hardness increased by 5 times compared to the substrate	High-temperature wear and corrosion not examined	Saroj et al. [51]
TIG cladding	WC-10Co-4Cr	Hardness improved by 1200HV and wear-rate reduced by 60%	The effect of multilayer or overlapping tracks not analyzed	Singh et al. [52]
Cold Metal Transfer	Nickel-based	Hardness increased by 3 times and wear loss decreased by 50%	Corrosion and erosion resistance not explored.	Tang [53]
Magnetron Sputtering	AlFeCrNiMo	Friction coefficient reduced by 40% and corrosion rate dropped 50%	Mechanical performance not quantitatively analyzed	Zeng et al. [54]
Laser Cladding	WC	Hardness enhanced to 1100HV and COF reduced from 0.65 to 0.25	Fatigue and corrosion performance not reported	Chakraborty et al. [55]
Laser Cladding	Colmonoy-6 and Stellite-6	Wear resistance improved by 49 times and hardness incresed to 950 HV	Corrosion and thermal fatigue behavior not discussed	Jeyaprakash et al. [56]
Laser Cladding	Ni60-Ti3SiC2	COF decreased from 0.6 to 0.3 and hardness increased to 900HV	Oxidation resistance not evaluated	Liu et al. [57]
Laser Cladding	CoCrMoSi	Hardness increased from 220HV to 850HV and wear-rate reduced by 60%	Corrosion and fatigue behavior unaddressed	lu et al. [58]
Laser Cladding	Tribaloy T-700, PAC 718 and MEC 41- C	Hardness improved to 1000HV ($\approx$ 5 times that of the substrate)	Corrosion and fatigue behavior unaddressed	More et al. [59]
Laser Cladding	NiCoCrAlY	Oxidation rate reduced by 35%	Long-term cyclic oxidation tests unaddressed	Nie et al. [60]
HVOF spraying	WC-CoCr, WC-Ni, WC-Cr3C2-Ni	Abrasive wear resistance increased by 4 to 90 times and hardness improved to 1200HV	Corrosion and fatigue behavior unaddressed	Qiao et al. [61]
TIG cladding	WC-10Co-4Cr	Hardness increased to 1150HV and wear rate reduced by 60%	Fatigue and corrosion performance not analyzed	Singh et al. [62]

Laser Cladding	WC-Cr	Hardness increased to 1050HV and dilution minimized to less than 8%	Coating porosity and bonding strength not analyzed	singh et al. [63]
Laser Cladding	AISI 316	Dilution controlled below 10% with formation of cellular-dendritic structure	Mechanical and wear not analyzed	Torres et al. [64]
Laser Cladding	Al2O3@Ni	Hardness increased to 917HV and wear rate reduced by 65%	Corrosion behavior not analyzed	Zhang et al. [65]
MIG Cladding	Ni-Cr-Si-B	Wear resistance increased by 20 times and microhardness increased by 3 times	Long-term oxidation and corrosion tests not performed	Zunake et al. [66]
Laser Cladding	FeCrAlNbNi	Hardness increased to 950HV and wear rate reduced by 70%	Corrosion and oxidation resistance not analyzed.	Cui et al. [67]
Plasma Arc Cladding	Ni-WC	Hardness increased to 1200HV and wear resistance improved by 2.5 times	Corrosion and oxidation resistance not analyzed	Fan et al. [68]
Laser Cladding	CoCrNiMo and CoCrNiMoBC	Hardness increased to 1000HV, wear rate decreased by 60% and corrosion rate decreased by 50%	Fatigue and oxidation properties not examined	Jiang et al. [69]
Plasma Arc Cladding	NiCrBSi and NiCrBSi-WC	Slurry abrasive resistance to wear increased by 65% and hardness increased to 850HV	High-temperature wear behavior not assessed	Kalyankar et al. [70]
Laser Cladding	NiCoCrAlY	Oxidation resistance decreased by 30%	Mechanical performance not quantitatively analyzed	Li et al. [71]
Laser Cladding	stellite-6	Hardness increased to 950HV and wear rate decreased by 45%	Thermal fatigue and corrosion not investigated	Singh et al. [72]
Laser Cladding	TiN	Hardness increased by 6 times that of the substrate	Thermal fatigue and corrosion not investigated	Tyagi et al. [73]
Microwave Cladding	Ni-CrC	Micro-hardness increased by approximately 47.6%	Thermal fatigue and corrosion not investigated	Dwivedi et al. [74]
Microwave Cladding	Ni-Si-La2O3	COF reduced from 0.6 to 0.3 and wear rate decreased by 40%	Oxidation and corrosion behavior not investigated	Dwivedi et al. [75]
Plasma Arc Cladding	Stellite 6	Hardness increased to 900HV and corrosion decreased by 50%	Adhesion strength and wear under elevated temperatures not evaluated	Sarangi et al. [76]
Laser Cladding	FeCoCrNiTi (High-Entropy Alloy)	Hardness improved to 780HV (≈ 3.5 times that of the substrate) and corrosion decreased by 60% with refined microstructure	Long-term corrosion-wear behavior not investigated	Zheng et al. [77]
Laser Cladding	Fe60	Hardness increased from 420HV to 720HV and wear-rate decreased by 45%	Wear and corrosion mechanisms post-heat treatment not investigated	Du et al. [78]
Gas Tungsten Arc (TIG) Cladding	CoCrFeMoNi	Hardness increased to 950HV (≈ 4 times that of the substrate) and corrosion resistance increased by 50%	Effect of multi-pass overlapping and residual stress not analyzed	Liu et al. [79]
Laser Cladding	Stellite 12	Hardness increased to 880HV, friction coefficient reduced by 35% and wear rate decreased by 55%	Oxidation and fatigue life under cyclic loads not evaluated	Wang et al. [80]
Argon Arc Cladding	TiB2-CoTi Composite	Hardness increased to 1200HV, wear rate reduced by 60% and COF reduced by 40%.	High-temperature oxidation and corrosion not evaluated	Kumar et al. [81]

Gas Tungsten Arc Cladding	CoCrFeNi + Sn/Ti	Hardness increased to 1000HV and wear resistance increased by 65%	Tribocorrosion and oxidation behavior not studied	Jaturapronperm et al. [82]
Microwave Cladding	Ni + TiO ₂	Hardness increased to 750HV (i.e. 3.5 times that of the substrate) and COF reduced by 40%	Corrosion-oxidation behavior not studied	Sharma et al. [83]
Microwave Cladding	Ni + 15% SiC	Hardness enhanced by 60% and wear resistance increased by 45%	Adhesion strength and oxidation not studied	Dwivedi et al. [84]
Microwave Cladding	Si + Ni + TiO ₂	Hardness increased by 720HV and wear resistance increased by 50%	Thermal fatigue and corrosion behaviour not explored	Dwivedi et al. [85]
Laser Cladding (Magnetic Field-Assisted)	Nickel Alloy GH3625	Hardness increased by 400%, friction coefficient reduced by 30% and wear-rate decreased by 50%	Thermal fatigue and corrosion behaviour not explored	Shi et al. [86]

2. SELECTION OF CLADDING MATERIALS FOR OPTIMAL COATING PERFORMANCE

An important part of the coating process is selecting the right cladding materials. Insufficient adhesion to the substrate and failure might be caused by improper material selection. Assessing how closely the coating's chemical and physical characteristics match those of the substrate is crucial when choosing coating materials. The elasticity modulus, melting temperature, wettability, and coefficient of thermal expansion are important physical properties that affect coating performance. These characteristics should be comparable or closely aligned between the coating materials and the substrate. Problems including delamination, high thermal residual stress, poor bonding, cracking, void formation, segregation, uneven coating, and substrate evaporation from overheating might arise if there is a significant mismatch. Therefore, careful material selection is critical to ensuring optimal hardness, wear resistance, and corrosion protection in surface engineering. The following sections will cover various approaches to designing and selecting coating materials.

2.1 Applying metallic, ceramic, and composite coatings to enhance mechanical performance

Metal coatings and alloy layers are often applied to enhance the characteristics of materials like austenitic stainless steel. Combinations of two or more metallic elements, known as alloys, usually have better qualities than the individual metals. Common coatings for austenitic stainless steel include transition metal alloys, Ni-Ti (Nickel-

Titanium) alloys, and other hard metal alloys. For example, Saroj et al. [51] applied the gas tungsten arc (GTA) coating method combined with a pre-placed powder technique to deposit an Inconel 825 cladding on AISI 304 steel. The upper and central regions of the cladding exhibited a consistent cellular microstructure, while the interface displayed a columnar dendritic pattern. The cladding layer achieved hardness between 300 and 350 HV, which is significantly higher than the base material's 220 HV. This enhancement also led to improved wear resistance against a hardened steel ball. Similarly, Zeng et al. [87] coated AISI 304 steel with a layer of Ni-Ti alloy by GTA cladding. This layer enhanced the corrosion and cavitation-resistance of the material, particularly in marine environments. Two thicknesses, 2 mm and 1.2 mm, were examined, with the thicker layer showing better performance. The development of an oxide film contributed to enhanced resistance to both wear and corrosion, with the Ni-Ti coating outperforming the uncoated stainless steel. In another experiment, Krishnakumar and Saravanan [88] used GTA surfacing on AISI 304 coated with Ti-W alloy layer under argon and nitrogen atmospheres. The hardness of the cladding reached 1968 HV in argon and increased to 2139 HV in nitrogen, both significantly higher than the 277 HV of the base material. The development of intermetallic compounds and a refined microstructure was associated with this increase in hardness. Additionally, both layers showed better wear and corrosion-resistance than the stainless steel substrate, particularly in Hank's salt solution, and the wear-rate in nitrogen was lower than in argon. Lastly, Shi et al. [89] fabricated Ni-Ti alloy layers on stainless steel using the TIG surfacing

technique, with and without a Ni interlayer. The Ni interlayer improved cavitations erosion resistance by reducing the formation of brittle Fe₂Ti phases and limiting crack propagation. As a result, the Ni-Ti alloy with the interlayer had better resistance to cavitations-erosion compared to the alloy layer without the interlayer, due to its enhanced elasticity and ability to suppress crack growth.

Ceramic materials are known for their extreme hardness due to their covalent bonding properties. When applied as a coating on stainless steel substrates, they enhance both the micro-hardness and resistance to wear of the surface. Ceramics used for such coatings include oxides, carbides, nitrides, and borides, with common materials being SiC, TiC, WC, TiB, TiN, TiO₂, and Al₂O₃. A TIG torch-assisted coating approach was used in research by Buytoz and Ulutan [90] to apply SiC ceramic powder to AISI 304 austenitic steel. They found that at lower powder concentrations, surface hardness ranged between 550 and 750 HV, which was connected to the formation of dendrites. With increased powder content, a hypereutectic microstructure developed, resulting in hardness values between 890 and 1210 HV due to the formation of M₇C₃ carbide. Rasool and Stack [91] used the GTA surfacing process to coat austenitic stainless steel with a TiC ceramic layer, observing improved micro-hardness and resistance to wear over the base material. Similarly, Sahoo et al. [92] applied a TiC coating on AISI 304 SS through the GTA method. In comparison to the substrate, they found that a TiC layer with improved hardness and resistance to wear was created at a lower current and higher scanning speed. Slower scanning and greater currents, however, diminished these characteristics.

Composite materials are made up of two distinct components: the matrix and the reinforcement. By combining a softer reinforcement phase with a harder one, the resulting composite material can display superior characteristics such as improved hardness, wear resistance, and stiffness. Generally, ceramics like oxides, carbides, nitrides, and borides are used as reinforcements, while metals like nickel, cobalt, iron, aluminum, titanium, copper, molybdenum, chromium, and zirconium act as matrix elements, particularly for forming composite coatings on stainless steel. In their study, Kumar

and Das [93] employed a gas tungsten arc (GTA) torch to coat AISI 304 SS with a mixture of cobalt and silicon carbide powders. The resulting coating featured phases including FeSi, SiC, CoSi₂, CoSi, Fe₂Si, and cobalt, achieving hardness values between 374 HV and 650 HV, significantly higher than the hardness of the substrate (i.e. 190 HV). Additionally, the coated layer exhibited much better resistance to wear than the stainless steel base material. Singh et al. [52, 94] created a composite coating using tungsten carbide (WC) as the reinforcement within a cobalt-chromium matrix, applied via a tungsten inert gas (TIG) cladding method on AISI 304. The findings demonstrated that the hard WC phase in the Co-Cr matrix was responsible for the better surface hardness and resistance to wear of the coated layer when compared to the original material. Kilic et al. [95] created a surface layer reinforced with silicon carbide in a nickel-boron-silicon matrix on AISI 304 SS using the GTA coating technique. This coating exhibited increased surface hardness and wear resistance due to the presence of dissolved silicon carbide within its dendritic microstructure. Hard metal carbides and borides were added to the SiC-reinforced nickel-boron-silicon metal matrix composite (MMC) to greatly increase its hardness and wear-resistance when compared to the AISI 304 substrate. The highest recorded hardness was 590 HV, which is 2.5 times higher than the substrate's. A composite coating consisting of titanium carbide with Inconel 825 matrix was applied on AISI 304 using GTA cladding by Saroj et al. [30]. They investigated how the coating's microstructure and mechanical performance were affected by the TiC content, coating thickness, and current. The nickel-based matrix exhibited excellent wettability with TiC, leading to strong metallurgical bonding. The coated layers reached a hardness of 1100 HV and showed a wear rate nearly seven times lower than the uncoated austenitic stainless steel. Sahoo and Masanta [96] produced a composite coating using nickel and titanium carbide powders on AISI 304 through GTA cladding. X-ray diffraction established the presence of titanium carbide and nickel-titanium intermetallic compounds. The coated surface demonstrated superior hardness and resistance to wear compared to the substrate, with nickel contributing to improved thermal and electrical conductivity. This resulted in a stable arc during the cladding

process, reduced energy demand for melting the powders, and enhanced bonding strength with the substrate. The coating hardness was recorded at 1300 HV, while its resistance to wear was 70 times greater than that of AISI 304. Key parameters like current and scanning speed significantly influenced the tribo-mechanical qualities of the coating. Heidarshenas et al. [97] developed a TiC/Cr₂₃C₆ cladding on AISI 304 using TIGC with Ti-cored wire and graphite powder. They found that higher currents increased the hardness and resistance to wear, while higher scanning speeds decreased them. The coating achieved a micro-hardness 4.5 times higher than AISI 304. The resistance to wear also improved by a factor of 4.5 compared to the substrate. This enhancement was linked to the formation of TiC and Cr₂₃C₆ phases. The coated layer exhibited a coefficient of friction of 0.35, which is nearly half that of the substrate material.

2.2. Applying nano-composite and high-entropy alloys for superior performance

Nano-composite refers to a composite material that includes at least one phase at the nanoscale, ranging from 1 to 100 nanometers. Typically, the reinforcing phases utilized for coatings are ceramic materials, such as oxides, carbides, borides, and nitrides. These reinforcement materials are incorporated as nanoparticles within the coating formulation to create nanocomposite coatings on metallic substrates. The inclusion of nanomaterials disrupts the movement of dislocations within the coating, leading to a reduction in grain size and an enhancement in the coating's properties and strength. Nanocomposite coatings offer superior characteristics compared to coatings made from Ni, Co, and Fe alloys. They exhibit high hardness, impressive fracture toughness, and strong resistance to corrosion, oxidation and wear, particularly under elevated temperatures. According to Singh et al. [52, 94], a nanocomposite coating comprising nano-WC and mixed powders of Co and Cr was applied to AISI 304 using the GTA coating technique. The results indicated that this coating achieved the highest micro-hardness and resistance to wear, attributed to the presence of WC nanoparticles within the Co-Cr matrix. The stand-off distance, scanning speed, and applied current were the main determinants of the tribo-mechanical

properties, whereas the argon flow rate had minimal impact on the microstructure and mechanical features. The applied current plays an important part in improving the microhardness and resistance to wear of the nanocomposite coating.

High entropy alloys are multi-element systems that consist of five or more different chemical elements, each contributing between 5% and 35% to the overall composition. This innovative approach to alloy design offers unique benefits. Due to features such as lattice distortion, high entropy effect, etc., these alloys exhibit excellent mechanical properties, as well as increased resistance to wear, corrosion, and oxidation at elevated temperatures. The high mixing entropy in high entropy alloys decreases the Gibbs free energy of chemical reactions. A reduction in Gibbs free energy leads to enhanced chemical reactivity of the materials, particularly as temperature rises. Huo et al. [98] applied a high entropy alloy coating to AISI 304 using a TIG torch coating technique with a mixture of Co-Fe-Ni-Cr-Mn-Nb powders. Their research identified a microstructure featuring a face-centered cubic (FCC) solid solution alongside a Nb-enriched Laves phase. During dry sliding testing, resistance to wear of the coating was noticeably higher than the base materials, mostly because of the hard Laves phases and the FCC solid solution. Furthermore, the FCC solid solution's grain development was inhibited by the coating's Nb addition. While the FCC phase increases toughness and lowers the risk of brittle failure, the Laves phase improves resistance to wear and plastic deformation. Consequently, under dry sliding circumstances, the high-entropy alloy coating exhibits remarkable resistance to wear due to the combined action of the Laves phase and FCC structure.

2.3. Applying solid lubricant coatings for enhanced durability

Solid lubricants play a crucial role in minimizing the friction coefficient and improving the resistance to wear of coatings. Their effectiveness as antifriction and anti-wear agents is attributed to their layered, hexagonal structure. These lubricants possess characteristics such as low density and low shear strength, which contribute to a decreased

friction coefficient. Commonly used solid lubricants as additives in coatings include MoS_2 , WS_2 , BaF_2 , h-BN, graphite, and CaF_2 . Sahoo and Masanta [29] utilized a GTA torch to deposit a layer of TiC-Ni metal matrix composite (MMC) with CaF_2 onto austenitic stainless steel. When tested against a hardened steel equivalent, they discovered that the coating had a lower friction coefficient and better resistance to wear than the underlying material. The self-fluxing properties of CaF_2 contribute to better heat retention in the coating area, serving as a solid lubricant and enhancing the tribological characteristics of the coating. The coating's hardness was recorded at 800 HV, but it decreased as the proportion of CaF_2 increased. Additionally, a higher dilution rate caused a decrease in coating hardness when the applied current was increased, while the CaF_2 content remained constant. At a CaF_2 content of 5 wt%, the coefficient of friction was recorded at 0.7, which decreased to 0.4 as the CaF_2 content increased.

3. MICROSTRUCTURAL BEHAVIOR OF THE COATINGS

The chemical composition of both the cladding material and the substrate has a significant impact on the coating's microstructural properties. Furthermore, the conditions established during the laser cladding process influence these microstructural characteristics. Analyzing the microstructure entails determining grain size and shape, the chemical composition of the cladding material, and the direction of grain structures within the heat-affected zone. These factors are vital for evaluating their effects on tribological and mechanical properties. Traditionally, metallographic techniques have been used to analyze the microstructure of these coatings. Several modern technologies are now available for investigating the microstructure and composition of distinct phases inside the coating. These methods include EPMA (electron probe microanalyzer), FESEM with EDS, and TEM, among others. Samples were polished using abrasive sheets to achieve a near-mirror finish, followed by diamond polishing. The microstructure was revealed through etching with either vilella or nital solution and subsequently examined under an optical microscope (OM). A significant portion of

research focuses on microstructural characteristics, with some recent studies specifically investigating carbon nanotube coatings.

4. ANALYSIS OF TRIBO-MECHANICAL CHARACTERISTICS OF THE COATINGS

The tribo-mechanical examination of the modified surface involved measuring microhardness and evaluating tribological performance.

4.1 Microhardness analysis

"Hardness" refers to a material's resistance to plastic deformation produced by processes such as indentation, scratching, and friction. To determine microhardness, a Vickers indenter was utilized in combination with a microhardness testing instrument. It is vital to note that around 70% of the study on laser cladding methods focuses on understanding the hardness characteristics of the coatings. Majumdar et al. [11] studied surface alloying as an approach for improving surface features while preserving the material's bulk properties. They utilized a laser to precisely heat titanium boride (TiB_2), which was alloyed with SS304 to increase its hardness and resistance to wear. Compared to the substrate AISI 304, which had a hardness of roughly 220 HV, the resulting clad layer exhibited a significant increase in hardness, reaching approximately 350 HV, while the gain in wear resistance was small. Sun et al. [99] used Cr-CrB₂ coating powder to coat SS304 substrate using laser surface alloying technique. The results showed significant increases in microhardness, resistance to wear, and corrosion resistance. On a steel substrate, Sahoo et al. [27] applied a TiC-reinforced composite layer using a Nd laser. SEM analysis showed the presence and deposition of TiC particles, and at peak power levels between 1 and 1.5, the coating dimensions were relatively small. The TiC-reinforced layer achieved an average hardness of 1200HV (6-times superior than the substrate). Zhao et al. [100] used a non-transferred arc plasma cladding technique to create a layer of Stellite Ni60 alloy coated on steel. According to the Vickers microhardness tests, the clad layer's maximum hardness was around 800 HV. A TiC-steel composite coating was deposited using argon arc cladding by Sahoo et al. [92] also examined the impact of input

current and scan speed on the microstructure and morphology of the coating. At a modest argon arc cladding input current of 60A, the maximum hardness of 1600HV was achieved. Detailed information regarding these hardness-focused studies can be found in Table 1.

4.2 Tribological properties analysis

When two solid surfaces engage in sliding or rolling contact, they experience a process called material degradation, commonly known as surface wear. This is a widespread challenge in various industrial fields. Wear involves multiple factors, including oxidation, abrasion, erosion, impact, and corrosion, either individually or in combination. The pin-on-disk tribometer is recognized as the leading and highly effective device for evaluating the tribological characteristics of materials. Wang et al. [101] examined how rare earth oxides affect the wear performance of Fe-based ceramics produced in situ, discovering an optimal Y2O3 concentration that improved the wear characteristics of the cladding. Tian et al. [102] created a Fe-Si-Mn-Ni-Cr alloy coating on steel using a 6-kW fiber laser through in situ deposition. Their findings indicated that the alloy coating comprised planar, dendritic, and equiaxed crystals, with the coefficient of friction (COF) and wear-rate (WR) being lower than that of SS304. They attributed the increased wear resistance of the coating to its self-accommodating stress feature. Yuan et al. [103] developed a dense WC/Ni-Al coating on the carbon steel using the plasma transferred arc (PTA) process. Their results showed that incorporating Fe into the Ni-Al/WC coating reduced the occurrence of fractures and facilitated the melting of WC particles into uniformly distributed small sizes within the Fe-rich dendritic structure. This even distribution of WC allowed the newly developed NiAl/WC-Fe5 clad layer to achieve superior COF and wear resistance compared to all other coatings tested. Saroj et al. [30] developed a composite coating made of Titanium carbide (TiC) and Inconel825 on steel using argon arc cladding technique. Their results showed that the coated layer's hardness had significantly increased, resulting in a sevenfold decrease in sliding abrasive wear compared to the uncoated steel. This advancement is critical for applications such as canister materials for high-level liquid waste storage and structural components in nuclear

settings, where wear is a significant source of material deterioration [66]. The studies are summarized in Table 1.

5. CONCLUSIONS AND FUTURE PROSPECTS

The introduction of innovative cladding designs for AISI 304 steel has successfully tackled the issue of achieving an optimal balance between wear resistance and toughness, a challenge often faced with traditional uniform cladding approaches. These advancements draw inspiration from highly efficient materials. Nevertheless, these new designs are currently limited by their relatively simplistic microstructural configurations and dependence on a single strengthening and toughening mechanism. This may impede possible improvements in resistance to wear, toughness, and hardness. Future research in this subject should focus on overcoming these constraints and discovering creative techniques to increase the resistance to wear of AISI 304 steel.

5.1 Implementation of Advanced Manufacturing Techniques in Cladding

Traditional surface modification procedures are used to increase the resistance to wear of AISI 304 steel by developing coatings with higher toughness and hardness. However, creating coatings with specified spatial patterns is a difficult operation, limiting their industrial applicability. Therefore, there is a need for advanced manufacturing technologies that can create wear-resistant coatings with appropriate shapes and designs. Future study can focus on adapting the hybrid cladding techniques to SS304, as no substantial studies have previously investigated. Investigating laser-induction or similar hybrid methods on SS304 may yield improvements in coating quality, metallurgical bonding, and wear and corrosion resistance [104]. Recently, 3D printing has gained popularity as a feasible method for producing coatings with increased toughness and hardness. This approach allows for exact control over microstructure design, resulting in higher efficiency compared to conventional methods. Furthermore, 3D printing allows for the manufacturing of near-net-shape items, reducing the need for additional material processing and increasing production efficiency.

5.2 Optimization of the process parameters

To develop wear-resistant cladding with improved toughness and hardness, a bionic structural design approach can be employed, focusing on multiscale strengthening and toughening. To optimise coating performance, it is necessary to improve the interface structure, distinct morphologies, diverse elements, and different levels inside the cladding. Additionally, new structural coatings should be designed concurrently with specific application needs and performance standards in mind, aiming to expand the application range of AISI 304 steel coatings.

5.3 Use of numerical simulation technology

Traditionally, material research and development used the "hypothesis formulation followed by experimental validation" technique. However, this method is increasingly time-consuming and labor-intensive in light of the growing industrial demand for innovative materials. With advancements in computer technology, numerical simulation and computation have become crucial for materials research. These techniques can be utilized to analyze the design and mechanical characteristics of coatings, thus overcoming the limitations of experimental setups.

Based on this, the authors outline a technical roadmap for creating wear-resistant coatings with enhanced toughness and hardness on AISI 304 steel surfaces.

REFERENCES

- [1] P. Murkute, S. Pasebani, and O. B. Isgor, "Production of corrosion-resistant 316L stainless steel clads on carbon steel using powder bed fusion-selective laser melting," *Journal of Materials Processing Technology*, vol. 273, p. 116243, May 2019, doi: [10.1016/j.jmatprotec.2019.05.024](https://doi.org/10.1016/j.jmatprotec.2019.05.024).
- [2] C. V. Haden, G. Zeng, F. M. Carter, C. Ruhl, B. A. Krick, and D. G. Harlow, "Wire and arc additive manufactured steel: Tensile and wear properties," *Additive Manufacturing*, vol. 16, pp. 115–123, May 2017, <https://doi.org/10.1016/j.addma.2017.05.010>.
- [3] S. Khara, S. Choudhary, S. Sangal, and K. Mondal, "Corrosion resistant Cr-coating on mild steel by powder roll bonding," *Surface and Coatings Technology*, vol. 296, pp. 203–210, Apr. 2016, doi: [10.1016/j.surfcoat.2016.04.033](https://doi.org/10.1016/j.surfcoat.2016.04.033).
- [4] J. I. Arrizubieta, A. Lamikiz, M. Cortina, E. Ukar, and A. Alberdi, "Hardness, grain size and porosity formation prediction on the Laser Metal Deposition of AISI 304 stainless steel," *International Journal of Machine Tools and Manufacture*, vol. 135, pp. 53–64, Aug. 2018, doi: [10.1016/j.ijmachtools.2018.08.004](https://doi.org/10.1016/j.ijmachtools.2018.08.004).
- [5] J. Kaur, V. Mangla, J. Singh, S. Kumar, and N. Srivastava, "Cladding of stainless steel (SS304) on aluminium alloy (AA1100) by explosive welding," *Materials Today Proceedings*, vol. 5, no. 9, pp. 19136–19139, Jan. 2018, doi: [10.1016/j.matpr.2018.06.267](https://doi.org/10.1016/j.matpr.2018.06.267).
- [6] G. Muvvala, D. P. Karmakar, and A. K. Nath, "Online assessment of TiC decomposition in laser cladding of metal matrix composite coating," *Materials & Design*, vol. 121, pp. 310–320, Feb. 2017, doi: [10.1016/j.matdes.2017.02.061](https://doi.org/10.1016/j.matdes.2017.02.061).
- [7] O. P. Oladijo, M. H. Mathabatha, A. P. I. Popoola, and T. P. Ntsoane, "Characterization and corrosion behaviour of plasma sprayed Zn-Sn alloy coating on mild steel," *Surface and Coatings Technology*, vol. 352, pp. 654–661, May 2017, doi: [10.1016/j.surfcoat.2017.04.029](https://doi.org/10.1016/j.surfcoat.2017.04.029).
- [8] R. L. Deuis, J. M. Yellup, and C. Subramanian, "Metal-matrix composite coatings by PTA surfacing," *Composites Science and Technology*, vol. 58, no. 2, pp. 299–309, Jan. 1998, doi: [10.1016/s0266-3538\(97\)00131-0](https://doi.org/10.1016/s0266-3538(97)00131-0).
- [9] M. Venter, O. P. Oladijo, V. Luzin, L. A. Cornish, and N. Sacks, "Performance characterization of metallic substrates coated by HVOF WC-Co," *Thin Solid Films*, vol. 549, pp. 330–339, Aug. 2013, doi: [10.1016/j.tsf.2013.08.075](https://doi.org/10.1016/j.tsf.2013.08.075).
- [10] F. Akhtar and S. J. Guo, "Microstructure, mechanical and fretting wear properties of TiC-stainless steel composites," *Materials Characterization*, vol. 59, no. 1, pp. 84–90, Dec. 2006, doi: [10.1016/j.matchar.2006.10.021](https://doi.org/10.1016/j.matchar.2006.10.021).
- [11] J. D. Majumdar, B. R. Chandra, and I. Manna, "Laser composite surfacing of AISI 304 stainless steel with titanium boride for improved wear resistance," *Tribology International*, vol. 40, no. 1, pp. 146–152, 2007, doi: [10.1016/j.triboint.2006.04.006](https://doi.org/10.1016/j.triboint.2006.04.006).
- [12] R. Singh, M. Kumar, D. Kumar, and S. K. Mishra, "Erosion and Corrosion Behavior of Laser Cladded Stainless Steels with Tungsten Carbide," *Journal of Materials Engineering and Performance*, vol. 21, no. 11, pp. 2274–2282, Feb. 2012, doi: [10.1007/s11665-012-0170-y](https://doi.org/10.1007/s11665-012-0170-y).

- [13] J. D. Majumdar and I. Manna, "Laser surface alloying of AISI 304-stainless steel with molybdenum for improvement in pitting and erosion-corrosion resistance," *Materials Science and Engineering A*, vol. 267, no. 1, pp. 50–59, Jul. 1999, doi: [10.1016/S0921-5093\(99\)00053-2](https://doi.org/10.1016/S0921-5093(99)00053-2).
- [14] K. Ushashri and M. Masanta, "Hard TiC coating on AISI304 steel by laser surface engineering using pulsed ND:YAG Laser," *Materials and Manufacturing Processes*, vol. 30, no. 6, pp. 730–735, Oct. 2014, doi: [10.1080/10426914.2014.973593](https://doi.org/10.1080/10426914.2014.973593).
- [15] M. F. McGuire, *Stainless Steels for Design Engineers*. Materials Park, OH, USA: ASM International, 2008
- [16] M. Masanta, S. M. Shariff, and A. R. Choudhury, "A comparative study of the tribological performances of laser clad TiB₂-TiC-Al₂O₃ composite coatings on AISI 1020 and AISI 304 substrates," *Wear*, vol. 271, no. 7–8, pp. 1124–1133, May 2011, doi: [10.1016/j.wear.2011.05.009](https://doi.org/10.1016/j.wear.2011.05.009).
- [17] G. Ramírez, E. Jiménez-Piqué, A. Mestra, M. Vilaseca, D. Casellas, and L. Llanes, "A comparative study of the contact fatigue behavior and associated damage micromechanisms of TiN- and WC:H-coated cold-work tool steel," *Tribology International*, vol. 88, pp. 263–270, Apr. 2015, doi: [10.1016/j.triboint.2015.03.036](https://doi.org/10.1016/j.triboint.2015.03.036).
- [18] R. Ranjan and A. K. D. K. Das, "Improving the Resistance to Wear and Mechanical Characteristics of Cladding Layers on Titanium and its Alloys: A Review," *Tribology in Industry*, vol. 45, no. 1, pp. 136–152, Mar. 2023, doi: [10.24874/ti.1416.12.22.03](https://doi.org/10.24874/ti.1416.12.22.03).
- [19] C. Sudha, P. Shankar, R. V. S. Rao, R. Thirumurugesan, M. Vijayalakshmi, and B. Raj, "Microchemical and microstructural studies in a PTA weld overlay of Ni-Cr-Si-B alloy on AISI 304L stainless steel," *Surface and Coatings Technology*, vol. 202, no. 10, pp. 2103–2112, Sep. 2007, doi: [10.1016/j.surfcoat.2007.08.063](https://doi.org/10.1016/j.surfcoat.2007.08.063).
- [20] S. Anandan, S. Pityana, and J. D. Majumdar, "Structure-property-correlation in laser surface alloyed AISI 304 stainless steel with WC+Ni+NiCr," *Materials Science and Engineering A*, vol. 536, pp. 159–169, Dec. 2011, doi: [10.1016/j.msea.2011.12.095](https://doi.org/10.1016/j.msea.2011.12.095).
- [21] G. M. Balamurugan, M. Duraiselvam, and V. Anandakrishnan, "Comparison of high temperature wear behaviour of plasma sprayed WC-Co coated and hard chromium plated AISI 304 austenitic stainless steel," *Materials & Design (1980-2015)*, vol. 35, pp. 640–646, Oct. 2011, doi: [10.1016/j.matdes.2011.10.012](https://doi.org/10.1016/j.matdes.2011.10.012).
- [22] C.-H. Hsu, K.-H. Huang, and Y.-H. Lin, "Microstructure and wear performance of arc-deposited Ti-N-O coatings on AISI 304 stainless steel," *Wear*, vol. 306, no. 1–2, pp. 97–102, Jul. 2013, doi: [10.1016/j.wear.2013.07.005](https://doi.org/10.1016/j.wear.2013.07.005).
- [23] P. Sharma and J. D. Majumdar, "Microstructural characterization and Properties Evaluation of Ni-Based hardfaced coating on AISI 304 stainless steel by high velocity oxyfuel coating technique," *Metallurgical and Materials Transactions A*, vol. 44, no. 1, pp. 372–380, Sep. 2012, doi: [10.1007/s11661-012-1407-y](https://doi.org/10.1007/s11661-012-1407-y).
- [24] G. Singh, H. Singh, and B. S. Sidhu, "Corrosion behavior of plasma sprayed hydroxyapatite and hydroxyapatite-silicon oxide coatings on AISI 304 for biomedical application," *Applied Surface Science*, vol. 284, pp. 811–818, Aug. 2013, doi: [10.1016/j.apsusc.2013.08.013](https://doi.org/10.1016/j.apsusc.2013.08.013).
- [25] J. S. Grewal, B. S. Sidhu, and S. Prakash, "High temperature erosion performance of nanostructured and conventional TiAlN coatings on AISI-304 boiler steel substrate," *Transactions of the Indian Institute of Metals*, vol. 67, no. 6, pp. 889–902, May 2014, doi: [10.1007/s12666-014-0413-8](https://doi.org/10.1007/s12666-014-0413-8).
- [26] P. Xu, C. Lin, C. Zhou, and X. Yi, "Wear and corrosion resistance of laser cladding AISI 304 stainless steel/Al₂O₃ composite coatings," *Surface and Coatings Technology*, vol. 238, pp. 9–14, Oct. 2013, doi: [10.1016/j.surfcoat.2013.10.028](https://doi.org/10.1016/j.surfcoat.2013.10.028).
- [27] C. K. Sahoo and M. Masanta, "Effect of pulse laser parameters on TiC reinforced AISI 304 stainless steel composite coating by laser surface engineering process," *Optics and Lasers in Engineering*, vol. 67, pp. 36–48, 2015, doi: [10.1016/j.optlaseng.2014.10.010](https://doi.org/10.1016/j.optlaseng.2014.10.010).
- [28] S. J. Algodí, J. W. Murray, M. W. Fay, A. T. Clare, and P. D. Brown, "Electrical discharge coating of nanostructured TiC-Fe cermets on 304 stainless steel," *Surface and Coatings Technology*, vol. 307, pp. 639–649, Sep. 2016, doi: [10.1016/j.surfcoat.2016.09.062](https://doi.org/10.1016/j.surfcoat.2016.09.062).
- [29] C. K. Sahoo and M. Masanta, "Microstructure and mechanical properties of TiC-Ni coating on AISI304 steel produced by TIG cladding process," *Journal of Materials Processing Technology*, vol. 240, pp. 126–137, 2017, doi: [10.1016/j.jmatprotec.2016.09.018](https://doi.org/10.1016/j.jmatprotec.2016.09.018).
- [30] S. Saroj, C. K. Sahoo, and M. Masanta, "Microstructure and mechanical performance of TiC-Inconel825 composite coating deposited on AISI 304 steel by TIG cladding process," *Journal of Materials Processing Technology*, vol. 249, pp. 490–501, Jun. 2017, doi: [10.1016/j.jmatprotec.2017.06.042](https://doi.org/10.1016/j.jmatprotec.2017.06.042).

- [31] S. Hajare and C. L. Gogte, "Comparative study of wear behaviour of Thermal Spray HVOF coating on 304 SS," *Materials Today Proceedings*, vol. 5, no. 2, pp. 6924–6933, Jan. 2018, doi: [10.1016/j.matpr.2017.11.354](https://doi.org/10.1016/j.matpr.2017.11.354).
- [32] J. Lin, C. Chen, M. Zhang, and S. Wang, "The effects of heat treatment on microstructure and mechanical properties of Tribaloy 400 coatings deposited by laser cladding," *Journal of Materials Engineering and Performance*, vol. 27, no. 12, pp. 6339–6348, Nov. 2018, doi: [10.1007/s11665-018-3762-3](https://doi.org/10.1007/s11665-018-3762-3).
- [33] Y.-F. Liu *et al.*, "Microstructure and dry-sliding wear properties of TiC/CaF₂/γ-Ni self-lubricating wear-resistant composite coating produced by co-axial powder feeding plasma transferred arc (PTA) cladding process," *Surface and Coatings Technology*, vol. 345, pp. 61–69, Apr. 2018, doi: [10.1016/j.surfcoat.2018.04.003](https://doi.org/10.1016/j.surfcoat.2018.04.003).
- [34] K. B. Sachidananda, K. Mahesha, and A. Dey, "Effect of powder particle size on vibration damping behaviour of plasma sprayed alumina (Al₂O₃) coating on AISI 304 stainless steel substrate," *Ceramics International*, vol. 44, no. 1, pp. 158–163, Sep. 2017, doi: [10.1016/j.ceramint.2017.09.153](https://doi.org/10.1016/j.ceramint.2017.09.153).
- [35] X. Shi, K. Yu, L. Jiang, C. Li, Z. Li, and X. Zhou, "Microstructural characterization of Ni-201 weld cladding onto 304 stainless steel," *Surface and Coatings Technology*, vol. 334, pp. 19–28, Nov. 2017, doi: [10.1016/j.surfcoat.2017.11.023](https://doi.org/10.1016/j.surfcoat.2017.11.023).
- [36] Y. Xi *et al.*, "Residual stress and microstructure effects on mechanical, tribological and electrical properties of TiN coatings on 304 stainless steel," *Ceramics International*, vol. 44, no. 13, pp. 15851–15858, Jun. 2018, doi: [10.1016/j.ceramint.2018.05.266](https://doi.org/10.1016/j.ceramint.2018.05.266).
- [37] L. H. R. Apolinario *et al.*, "Predominant solidification modes of 316 austenitic stainless steel coatings deposited by laser cladding on 304 stainless steel substrates," *Metallurgical and Materials Transactions A*, vol. 50, no. 8, pp. 3617–3628, May 2019, doi: [10.1007/s11661-019-05293-y](https://doi.org/10.1007/s11661-019-05293-y).
- [38] J. Dong *et al.*, "Laser induced titanium and tungsten coating on 304 stainless steel surfaces for wear resistant improvement," *MATEC Web of Conferences*, vol. 278, p. 02002, Jan. 2019, doi: [10.1051/mateconf/201927802002](https://doi.org/10.1051/mateconf/201927802002).
- [39] J. Li, L. Pan, Q. Fu, Y. Zhou, and N. Guo, "Wettability and corrosion behavior of a Ni coating on 304 stainless steel surface," *Surface and Coatings Technology*, vol. 357, pp. 740–747, Oct. 2018, doi: [10.1016/j.surfcoat.2018.10.050](https://doi.org/10.1016/j.surfcoat.2018.10.050).
- [40] H. Liang *et al.*, "Microstructures and wear resistance of ALCRFENI2W0.2NBX High-Entropy alloy coatings prepared by laser cladding," *Journal of Thermal Spray Technology*, vol. 28, no. 6, pp. 1318–1329, Aug. 2019, doi: [10.1007/s11666-019-00901-0](https://doi.org/10.1007/s11666-019-00901-0).
- [41] S. Praveen and A. Arjunan, "Parametric optimisation of high-velocity oxy-fuel nickel-chromium-silicon-boron and aluminium-oxide coating to improve erosion wear resistance," *Materials Research Express*, vol. 6, no. 9, p. 096560, Jul. 2019, doi: [10.1088/2053-1591/ab301c](https://doi.org/10.1088/2053-1591/ab301c).
- [42] Q. Zhang, Z. Wang, F. Hu, and Z. Song, "Preparation of thin NiCrBSi laser cladding layers with no microcracking and low dilution," *Journal of Laser Applications*, vol. 31, no. 3, Aug. 2019, doi: [10.2351/1.5087773](https://doi.org/10.2351/1.5087773).
- [43] F. Movassagh-Alanagh and M. Mahdavi, "Improving wear and corrosion resistance of AISI 304 stainless steel by a multilayered nanocomposite Ti/TiN/TiSiN coating," *Surfaces and Interfaces*, vol. 18, p. 100428, Dec. 2019, doi: [10.1016/j.surfin.2019.100428](https://doi.org/10.1016/j.surfin.2019.100428).
- [44] S. Balaguru, M. Abid, and M. Gupta, "Investigations on different hardfacing processes for High temperature applications of Ni-Cr-B-Si alloy hardfaced on austenitic stainless steel components," *Journal of Materials Research and Technology*, vol. 9, no. 5, pp. 10062–10072, Jul. 2020, doi: [10.1016/j.jmrt.2020.07.010](https://doi.org/10.1016/j.jmrt.2020.07.010).
- [45] Bansal *et al.*, "Erosive wear behaviour of HVOF-sprayed Ni-20Cr203 coating on pipeline materials," *International Journal of Refractory Metals and Hard Materials*, vol. 92, p. 105332, Jul. 2020, doi: [10.1016/j.ijrmhm.2020.105332](https://doi.org/10.1016/j.ijrmhm.2020.105332).
- [46] Q. Cheng *et al.*, "Microstructure, oxidation resistance and mechanical properties of stellite 12 composite coating doped with submicron TiC/B₄C by laser cladding," *Surface and Coatings Technology*, vol. 395, p. 125810, Apr. 2020, doi: [10.1016/j.surfcoat.2020.125810](https://doi.org/10.1016/j.surfcoat.2020.125810).
- [47] Imak, A., Kilic, M., Kirik, I., Kavak, Y.B. and Balalan, Z., 2020. "PTA coating of austenitic stainless steels with NiAl-Al₂O₃+ TiB₂ powders," *Journal of Materials And Electronic Devices*, vol. 3, no. 1, pp. 26-29, 2020.
- [48] C.-S. OuYang, X.-B. Liu, Y.-S. Luo, J. Liang, M. Wang, and D.-Q. Chen, "Preparation and high temperature tribological properties of laser in-situ synthesized self-lubricating composite coating on 304 stainless steel," *Journal of Materials Research and Technology*, vol. 9, no. 4, pp. 7034–7046, Jun. 2020, doi: [10.1016/j.jmrt.2020.05.008](https://doi.org/10.1016/j.jmrt.2020.05.008).

- [49] Pizzatto, M. F. Teixeira, A. Rabelo, T. Falcade, and A. Scheid, "Microstructure and wear behavior of NBC-Reinforced NI-Based alloy composite coatings by laser cladding," *Materials Research*, vol. 24, no. 3, Jan. 2021, doi: [10.1590/1980-5373-mr-2020-0447](https://doi.org/10.1590/1980-5373-mr-2020-0447).
- [50] Sahu, A. Raheem, M. Masanta, and C. K. Sahoo, "On the constancy in wear characteristic of large area TiC-Ni coating developed by overlapping of TIG arc scanning," *Tribology International*, vol. 151, p. 106501, Jun. 2020, doi: [10.1016/j.triboint.2020.106501](https://doi.org/10.1016/j.triboint.2020.106501).
- [51] S. Saroj, A. Sahu, and M. Masanta, "Geometrical assessment and mechanical characterization of single-line Inconel 825 layer fabricated on AISI 304 steel by TIG cladding method," *Surfaces and Interfaces*, vol. 20, p. 100631, Aug. 2020, doi: [10.1016/j.surfint.2020.100631](https://doi.org/10.1016/j.surfint.2020.100631).
- [52] J. Singh, L. Thakur, and S. Angra, "An investigation on the parameter optimization and abrasive wear behaviour of nanostructured WC-10Co-4Cr TIG weld cladding," *Surface and Coatings Technology*, vol. 386, p. 125474, Feb. 2020, doi: [10.1016/j.surfcoat.2020.125474](https://doi.org/10.1016/j.surfcoat.2020.125474).
- [53] X. Tang, S. Zhang, X. Cui, C. Zhang, Y. Liu, and J. Zhang, "Tribological and cavitation erosion behaviors of nickel-based and iron-based coatings deposited on AISI 304 stainless steel by cold metal transfer," *Journal of Materials Research and Technology*, vol. 9, no. 3, pp. 6665–6681, May 2020, doi: [10.1016/j.jmrt.2020.04.064](https://doi.org/10.1016/j.jmrt.2020.04.064).
- [54] Q. Zeng and Y. Xu, "A comparative study on the tribocorrosion behaviors of AlFeCrNiMo high entropy alloy coatings and 304 stainless steel," *Materials Today Communications*, vol. 24, p. 101261, May 2020, doi: [10.1016/j.mtcomm.2020.101261](https://doi.org/10.1016/j.mtcomm.2020.101261).
- [55] Chakraborty *et al.*, "Microstructures, wear and corrosion resistance of laser composite surfaced austenitic stainless steel (AISI 304 SS) with tungsten carbide," *Optics & Laser Technology*, vol. 134, p. 106585, Sep. 2020, doi: [10.1016/j.optlastec.2020.106585](https://doi.org/10.1016/j.optlastec.2020.106585).
- [56] N. Jeyaprakash, C.-H. Yang, and S.-P. Tseng, "Wear Tribo-Performances of laser cladding Colmonoy-6 and Stellite-6 micron layers on stainless steel 304 using YB:YAG Disk laser," *Metals and Materials International*, vol. 27, no. 6, pp. 1540–1553, Nov. 2019, doi: [10.1007/s12540-019-00526-6](https://doi.org/10.1007/s12540-019-00526-6).
- [57] Y.-F. Liu, S.-G. Zhuang, X.-B. Liu, C.-S. OuYang, Y. Zhu, and Y. Meng, "Microstructure evolution and high-temperature tribological behavior of Ti3SiC2 reinforced Ni60 composite coatings on 304 stainless steel by laser cladding," *Surface and Coatings Technology*, vol. 420, p. 127335, May 2021, doi: [10.1016/j.surfcoat.2021.127335](https://doi.org/10.1016/j.surfcoat.2021.127335).
- [58] H. Lu *et al.*, "The Gradient Microstructure and High-Temperature Wear behavior of the COCRMOSI coating by laser cladding," *Journal of Thermal Spray Technology*, vol. 30, no. 4, pp. 968–976, Apr. 2021, doi: [10.1007/s11666-021-01184-0](https://doi.org/10.1007/s11666-021-01184-0).
- [59] S. R. More, D. Bhatt V., J. Menghani, C. P. Paul, and G. R. Desale, "Laser cladding of PAC 718, Tribaloy T-700 and METCO 41 C hard facing powders on AISI SS 304L substrate," *International Journal of Engineering. Transactions B: Applications*, vol. 34, no. 1, Feb. 2021, doi: [10.5829/ije.2021.34.02b.20](https://doi.org/10.5829/ije.2021.34.02b.20).
- [60] J. Nie *et al.*, "Evolution of oxide layer during high-temperature oxidation of NiCoCrAlY coating via laser cladding on 304 stainless steel," *Materials Letters*, vol. 286, p. 129233, Dec. 2020, doi: [10.1016/j.matlet.2020.129233](https://doi.org/10.1016/j.matlet.2020.129233).
- [61] L. Qiao, Y. Wu, S. Hong, W. Long, and J. Cheng, "Wet abrasive wear behavior of WC-based cermet coatings prepared by HVOF spraying," *Ceramics International*, vol. 47, no. 2, pp. 1829–1836, Sep. 2020, doi: [10.1016/j.ceramint.2020.09.009](https://doi.org/10.1016/j.ceramint.2020.09.009).
- [62] J. Singh, L. Thakur, and S. Angra, "A study of tribological behaviour and optimization of WC-10Co-4Cr Cladding," *Surface Engineering*, vol. 37, no. 1, pp. 70–79, Mar. 2020, doi: [10.1080/02670844.2020.1745367](https://doi.org/10.1080/02670844.2020.1745367).
- [63] K. Singh *et al.*, "Experimental investigation and parametric optimization for minimization of dilution during direct laser metal deposition of tungsten carbide and cobalt powder mixture on SS304 substrate," *Powder Technology*, vol. 390, pp. 339–353, May 2021, doi: [10.1016/j.powtec.2021.05.056](https://doi.org/10.1016/j.powtec.2021.05.056).
- [64] E. A. Torres, L. H. R. Apolinario, H. R. Araujo, I. B. M. Picchi, and T. F. A. Santos, "Banding and microstructural features in laser cladding of a 304 substrate using 316 powder," *The International Journal of Advanced Manufacturing Technology*, vol. 112, no. 7–8, pp. 2327–2339, Jan. 2021, doi: [10.1007/s00170-020-06418-z](https://doi.org/10.1007/s00170-020-06418-z).
- [65] P.-X. Zhang, H. Yan, and Y.-H. Sun, "Microstructure, microhardness and corrosion resistance of laser cladding Al2O3@Ni composite coating on 304 stainless steel," *Journal of Materials Science*, vol. 56, no. 13, pp. 8209–8224, Jan. 2021, doi: [10.1007/s10853-020-05741-w](https://doi.org/10.1007/s10853-020-05741-w).
- [66] L. Zunake and V. D. Kalyankar, "On the performance of weld overlay characteristics of Ni-Cr-Si-B deposition on 304 ASS using synergetic pulse-GMAW process," *Science and Technology of Welding & Joining*, vol. 26, no. 2, pp. 106–115, Nov. 2020, doi: [10.1080/13621718.2020.1846935](https://doi.org/10.1080/13621718.2020.1846935).

- [67] Cui *et al.*, "Wear resistance of FECRALNBNI alloyed zone via laser surface alloying on 304 stainless steel," *Metals*, vol. 12, no. 3, p. 467, Mar. 2022, doi: [10.3390/met12030467](https://doi.org/10.3390/met12030467).
- [68] L. Fan, P. Ou, J. Rong, and X. Yu, "Preparation of high wear resistance nickel based WC coating by carefully adjusting interface structure," *Materials Research Express*, vol. 9, no. 8, p. 086402, Aug. 2022, doi: [10.1088/2053-1591/ac86ba](https://doi.org/10.1088/2053-1591/ac86ba).
- [69] Jiang *et al.*, "Wear and corrosion resistance of CoCrNi composite coatings by laser cladding," *China Foundry*, vol. 19, no. 6, pp. 535–543, Nov. 2022, doi: [10.1007/s41230-022-1192-1](https://doi.org/10.1007/s41230-022-1192-1).
- [70] V. D. Kalyankar and S. P. Wanare, "Comparative investigations on microstructure and slurry abrasive wear resistance of NICRBSI and NICRBSI-WC composite hardfacings deposited on 304 stainless steel," *Tribology in Industry*, vol. 44, no. 1, pp. 199–211, Jun. 2022, doi: [10.24874/ti.1075.03.21.05](https://doi.org/10.24874/ti.1075.03.21.05).
- [71] Y. Li *et al.*, "High-Temperature oxidation behavior of NICOCRALY coatings deposited by laser cladding on 304 stainless steel," *Metals and Materials International*, vol. 28, no. 2, pp. 412–420, Jan. 2021, doi: [10.1007/s12540-020-00927-y](https://doi.org/10.1007/s12540-020-00927-y).
- [72] A. R. Choudhury, "An approach towards energy and material efficient additive manufacturing: Multi-objective optimization of stellite-6 deposition on SS304," *Optics & Laser Technology*, vol. 148, p. 107799, Dec. 2021, doi: [10.1016/j.optlastec.2021.107799](https://doi.org/10.1016/j.optlastec.2021.107799).
- [73] R. Tyagi, S. Kumar, M. S. Raza, A. Tripathi, and A. K. Das, "Experimental study of laser cladding process and prediction of process parameters by artificial neural network (ANN)," *Journal of Central South University*, vol. 29, no. 10, pp. 3489–3502, Oct. 2022, doi: [10.1007/s11771-022-5170-y](https://doi.org/10.1007/s11771-022-5170-y).
- [74] S. P. Dwivedi, "Microstructure and Tribo-corrosion Behavior of Stainless Steel-304 Cladding with the Mixture of Nickel and Chromium Carbide by Microwave Energy," *Journal of the Institution of Engineers (India) Series D*, vol. 104, no. 2, pp. 689–697, Jan. 2023, doi: [10.1007/s40033-022-00439-6](https://doi.org/10.1007/s40033-022-00439-6).
- [75] S. P. Dwivedi *et al.*, "The microstructure and properties of NI-SI-LA2O3 coatings deposited on 304 stainless steel by microwave cladding," *Materials*, vol. 16, no. 6, p. 2209, Mar. 2023, doi: [10.3390/ma16062209](https://doi.org/10.3390/ma16062209).
- [76] S. Sarangi, A. K. Mishra, and S. Sahoo, "An experimental investigation on metallurgical and corrosion behavior of atmospheric plasma sprayed Stellite 6 powder on AISI 304 stainless steel," *Current Chemistry Letters*, vol. 12, no. 2, pp. 459–470, Jan. 2023, doi: [10.5267/j.ccl.2022.10.003](https://doi.org/10.5267/j.ccl.2022.10.003).
- [77] K. X. Zheng *et al.*, "Laser cladding of FeCoCrNiTi high-entropy alloy coatings to modulate the microstructure and enhance the tribo-corrosion behavior on 304 stainless steel," *Surface and Coatings Technology*, p. 132114, Apr. 2025, doi: [10.1016/j.surfcoat.2025.132114](https://doi.org/10.1016/j.surfcoat.2025.132114).
- [78] Y. Du, Y. Peng, Q. Liang, Z. Li, and J. Tu, "Effect of heat treatment on microstructure and mechanical properties of Fe60 coating by laser cladding on 304 stainless steel," *Journal of Materials Research and Technology*, vol. 29, pp. 2825–2834, Feb. 2024, doi: [10.1016/j.jmrt.2024.02.046](https://doi.org/10.1016/j.jmrt.2024.02.046).
- [79] N. Liu, Z. Lan, L. Liu, J. Dou, P. Guo, and X. Wang, "Optimizing 304 Stainless Steel Surface Performance with CoCrFeMoNi High-Entropy Alloy Coating via Gas Tungsten Arc Cladding," *Journal of Materials Engineering and Performance*, vol. 32, no. 20, pp. 9114–9120, Jan. 2023, doi: [10.1007/s11665-022-07781-6](https://doi.org/10.1007/s11665-022-07781-6).
- [80] R. Wang, C. Ouyang, Y. Li, C. Zhao, and Q. Bai, "Microstructure and tribological properties of Stellite 12 coating by laser cladding on 304 stainless steel surface," *Journal of Mechanical Science and Technology*, vol. 37, no. 8, pp. 3953–3960, Aug. 2023, doi: [10.1007/s12206-023-0711-3](https://doi.org/10.1007/s12206-023-0711-3).
- [81] R. Kumar and A. K. Das, "Experimental investigation on tribological performance of TiB2-COTI composite coating fabricated on AISI 304 stainless steel by argon arc cladding technique," *Journal of Thermal Spray Technology*, Nov. 2024, doi: [10.1007/s11666-024-01890-5](https://doi.org/10.1007/s11666-024-01890-5).
- [82] S. Jaturapronperm, P. Chiyasak, A. Taechamahaphan, C.-A. Huang, W. Wattanathana, and A. Rodchanarowan, "The effect of Sn and Ti addition in CoCrFeNi to prepare equiatomic high entropy alloy cladded on 304 stainless steels via gas tungsten arc cladding," *Materials Characterization*, p. 115048, Apr. 2025, doi: [10.1016/j.matchar.2025.115048](https://doi.org/10.1016/j.matchar.2025.115048).
- [83] S. Sharma, S. P. Dwivedi, C. Li, F. A. Awwad, M. I. Khan, and E. A. A. Ismail, "Unveiling of grain structure, porosity, phase distributions, microstructural morphology, surface hardness, and tribo-corrosion characteristics of nickel, and titanium dioxide-based SS-304 steel microwave composite coatings cladding," *Journal of Materials Research and Technology*, vol. 28, pp. 4299–4316, Dec. 2023, doi: [10.1016/j.jmrt.2023.12.144](https://doi.org/10.1016/j.jmrt.2023.12.144).
- [84] S. P. Dwivedi and S. Sharma, "Metallic cladding through microwave energy of the mixture of Ni and 15% SiC powder on AISI 304: A green approach in surface engineering," *Proceedings of the Institution of Mechanical Engineers Part E Journal of Process Mechanical Engineering*, vol. 238, no. 5, pp. 2545–2556, Apr. 2023, doi: [10.1177/09544089231167930](https://doi.org/10.1177/09544089231167930).

- [85] S. P. Dwivedi, P. Mukherjee, and S. Sharma, "Homogeneity, Hardness Distribution, and Metallurgical Behavior of SS-304 Cladding Surface with Si, Ni, and TiO₂," *Australian Journal of Mechanical Engineering*, vol. 22, no. 5, pp. 950–957, Apr. 2023, doi: [10.1080/14484846.2023.2203884](https://doi.org/10.1080/14484846.2023.2203884).
- [86] Z. Shi *et al.*, "Static transverse magnetic field assisted laser cladding of nickel alloy GH3625 for enhancing its microstructure, microhardness, friction and wear properties on 304 stainless steel substrate," *Optics & Laser Technology*, vol. 190, p. 113203, May 2025, doi: [10.1016/j.optlastec.2025.113203](https://doi.org/10.1016/j.optlastec.2025.113203).
- [87] Q. Zeng, K. Khanlari, and N. Lin, "An investigation on the possibility to improve the corrosion and cavitation resistance of SS304 steel by NiTi coatings," *International Journal of Modern Physics B*, vol. 35, no. 04, p. 2150057, Feb. 2021, doi: [10.1142/s0217979221500570](https://doi.org/10.1142/s0217979221500570).
- [88] M. Krishnakumar and R. Saravanan, "Surface alloying on austenitic stainless steel with titanium and tungsten using gas tungsten arc," *Engineering Research Express*, vol. 1, no. 2, p. 025005, Sep. 2019, doi: [10.1088/2631-8695/ab47b5](https://doi.org/10.1088/2631-8695/ab47b5).
- [89] Z.P. Shi, Z.B. Wang, J.Q. Wang, Y.X. Qiao, H.N. Chen, T.Y. Xiong and Y.G. Zheng, "Effect of NI interlayer on cavitation erosion resistance of NITI cladding by tungsten inert gas (TIG) surfacing process," *Acta Metallurgica Sinica (English Letters)*, vol. 33, no. 3, pp. 415–424, Oct. 2019, doi: [10.1007/s40195-019-00947-7](https://doi.org/10.1007/s40195-019-00947-7).
- [90] S. Buytoz and M. Ulutan, "In situ synthesis of SiC reinforced MMC surface on AISI 304 stainless steel by TIG surface alloying," *Surface and Coatings Technology*, vol. 200, no. 12–13, pp. 3698–3704, Apr. 2005, doi: [10.1016/j.surfcoat.2005.02.178](https://doi.org/10.1016/j.surfcoat.2005.02.178).
- [91] G. Rasool and M. M. Stack, "Wear maps for TiC composite based coatings deposited on 303 stainless steel," *Tribology International*, vol. 74, pp. 93–102, Feb. 2014, doi: [10.1016/j.triboint.2014.02.002](https://doi.org/10.1016/j.triboint.2014.02.002).
- [92] C. K. Sahoo, L. Soni, and M. Masanta, "Evaluation of microstructure and mechanical properties of TiC/TiC-steel composite coating produced by gas tungsten arc (GTA) coating process," *Surface and Coatings Technology*, vol. 307, pp. 17–27, Aug. 2016, doi: [10.1016/j.surfcoat.2016.08.056](https://doi.org/10.1016/j.surfcoat.2016.08.056).
- [93] A. Kumar and A. K. Das, "Evolution of microstructure and mechanical properties of Co-SiC tungsten inert gas cladded coating on 304 stainless steel," *Engineering Science and Technology an International Journal*, vol. 24, no. 3, pp. 591–604, Oct. 2020, doi: [10.1016/j.jestch.2020.10.001](https://doi.org/10.1016/j.jestch.2020.10.001).
- [94] J. Singh, L. Thakur, and S. Angra, "Abrasive wear behavior of WC-10Co-4Cr cladding deposited by TIG welding process," *International Journal of Refractory Metals and Hard Materials*, vol. 88, p. 105198, Jan. 2020, doi: [10.1016/j.jrmhm.2020.105198](https://doi.org/10.1016/j.jrmhm.2020.105198).
- [95] M. Kilic, A. Imak, and I. Kirik, "Surface Modification of AISI 304 Stainless Steel with NiBSi-SiC Composite by TIG Method," *Journal of Materials Engineering and Performance*, vol. 30, no. 2, pp. 1411–1419, Jan. 2021, doi: [10.1007/s11665-020-05378-5](https://doi.org/10.1007/s11665-020-05378-5).
- [96] C. K. Sahoo and M. Masanta, "Microstructure and tribological behaviour of TiC-Ni-CaF₂ composite coating produced by TIG cladding process," *Journal of Materials Processing Technology*, vol. 243, pp. 229–245, Dec. 2016, doi: [10.1016/j.jmatprotec.2016.12.028](https://doi.org/10.1016/j.jmatprotec.2016.12.028).
- [97] B. Heidarshenas, G. Hussain, and Mohammed. Asmael, "Development of a TiC/Cr₂₃C₆ Composite Coating on a 304 Stainless Steel Substrate through a Tungsten Inert Gas Process," *Coatings*, vol. 7, no. 6, p. 80, Jun. 2017, doi: [10.3390/coatings7060080](https://doi.org/10.3390/coatings7060080).
- [98] W. Y. Huo, H. F. Shi, X. Ren, and J. Y. Zhang, "Microstructure and wear behavior of COCRFEMNNBNI High-Entropy alloy coating by TIG cladding," *Advances in Materials Science and Engineering*, vol. 2015, pp. 1–5, Jan. 2015, doi: [10.1155/2015/647351](https://doi.org/10.1155/2015/647351).
- [99] G.F. Sun, Y.K. Zhang, M.K. Zhang, R. Zhou, K. Wang, C.S. Liu and K.Y. Luo, "Microstructure and corrosion characteristics of 304 stainless steel laser-alloyed with Cr–CrB₂," *Applied Surface Science*, vol. 295, pp. 94–107, Jan. 2014, doi: [10.1016/j.apsusc.2014.01.011](https://doi.org/10.1016/j.apsusc.2014.01.011).
- [100] C. Zhao, F. Tian, H.-R. Peng, and J.-Y. Hou, "Non-transferred arc plasma cladding of Stellite Ni60 alloy on steel," *Surface and Coatings Technology*, vol. 155, no. 1, pp. 80–84, Jun. 2002, doi: [10.1016/s0257-8972\(02\)00039-7](https://doi.org/10.1016/s0257-8972(02)00039-7).
- [101] X. H. Wang, S. S. Liu, M. Zhang, and K. L. Qu, "Effect of rare earth oxide on the microstructure and wear properties of in Situ-Synthesized Ceramics-Reinforced FE-Based laser cladding coatings," *Tribology Transactions*, vol. 63, no. 2, pp. 345–355, Dec. 2019, doi: [10.1080/10402004.2019.1694200](https://doi.org/10.1080/10402004.2019.1694200).
- [102] J. Tian, P. Xu, J. Chen, and Q. Liu, "Microstructure and phase transformation behaviour of a Fe/Mn/Si/Cr/Ni alloy coating by laser cladding," *Optics and Lasers in Engineering*, vol. 122, pp. 97–104, Jun. 2019, doi: [10.1016/j.optlaseng.2019.06.003](https://doi.org/10.1016/j.optlaseng.2019.06.003).

- [103] J. Yuan, Q. Wang, X. Liu, S. Lou, Q. Li, and Z. Wang, "Microstructures and high-temperature wear behavior of NiAl/WC-Fex coatings on carbon steel by plasma cladding," *Journal of Alloys and Compounds*, vol. 842, p. 155850, Jun. 2020, doi: [10.1016/j.jallcom.2020.155850](https://doi.org/10.1016/j.jallcom.2020.155850).
- [104] L. Qin *et al.*, "Microstructure, high-temperature cyclic oxidation, and hot corrosion behaviors of Inconel 718 alloy produced by laser-induction hybrid cladding," *Journal of Materials Research and Technology*, vol. 32, pp. 550–564, Jul. 2024, doi: [10.1016/j.jmrt.2024.07.200](https://doi.org/10.1016/j.jmrt.2024.07.200).